

Technical Data Sheet

# SCHULAMID® 612 GF 50

Polyamide 612  
Engineering Plastics

**Product Description**

50% glass fiber reinforced, Polyamide 612 compound with high strength after conditioning (available with different kinds of heat stabilization systems)

**General**

Filler / Reinforcement	• Glass Fiber, 50% Filler by Weight		
Features	• Chemical Resistant	• Heat Aging Resistant	
Processing Method	• Gas-Assisted Injection Molding	• Injection Molding	• Water-Assisted Injection Molding

Physical	Dry	Conditioned	Unit	Test Method
Density	1.51	--	g/cm <sup>3</sup>	ISO 1183/A
Water Absorption				ISO 62
Equilibrium, 73°F (23°C), 50% RH	0.90	--	%	
Viscosity Number (H <sub>2</sub> SO <sub>4</sub> (Sulphuric Acid))	110	--	cm <sup>3</sup> /g	ISO 307
Mechanical	Dry	Conditioned	Unit	Test Method
Tensile Modulus	2.26E+6 (15600)	1.84E+6 (12700)	psi (MPa)	ISO 527-2/1A/1
Tensile Stress (Break)	33400 (230)	27600 (190)	psi (MPa)	ISO 527-2/1A/5
Tensile Strain (Break)	3.0	3.6	%	ISO 527-2/1A/5
Flexural Modulus <sup>1</sup> (73°F (23°C))	2.03E+6 (14000)	--	psi (MPa)	ISO 178
Flexural Stress <sup>1</sup> (3.6% Strain, 73°F (23°C))	50800 (350)	--	psi (MPa)	ISO 178
Impact	Dry	Conditioned	Unit	Test Method
Charpy Notched Impact Strength				ISO 179/1eA
-40°F (-40°C)	6.7 (14)	--	ft·lb/in <sup>2</sup> (kJ/m <sup>2</sup> )	
73°F (23°C)	7.1 (15)	7.6 (16)	ft·lb/in <sup>2</sup> (kJ/m <sup>2</sup> )	
Charpy Unnotched Impact Strength				ISO 179/1eU
-40°F (-40°C)	No Break	--		
73°F (23°C)	No Break	34 ft·lb/in <sup>2</sup> (72 kJ/m <sup>2</sup> )	(kJ/m <sup>2</sup> )	
Thermal	Dry	Conditioned	Unit	Test Method
Heat Deflection Temperature				
66 psi (0.45 MPa), Unannealed	424 (218)	--	°F (°C)	ISO 75-2/Bf
264 psi (1.8 MPa), Unannealed	401 (205)	--	°F (°C)	ISO 75-2/ Af
Vicat Softening Temperature				
--	421 (216)	--	°F (°C)	ISO 306/A50
--	406 (208)	--	°F (°C)	ISO 306/B50

Technical Data Sheet

# SCHULAMID® 612 GF 50

Polyamide 612  
Engineering Plastics

Electrical	Dry	Conditioned	Unit	Test Method
Surface Resistivity	> 1.0E+15	> 1.0E+12	ohms	IEC 60093
Volume Resistivity	> 1.0E+13	> 1.0E+10	ohms·m	IEC 62631-3-1
Flammability	Dry	Conditioned	Unit	Test Method
Burning Rate				
0.0787 in (2.00 mm)	2.0 (50)	--	in/min (mm/min)	ISO 3795
0.0787 in (2.00 mm)	2.0 (50)	--	in/min (mm/min)	FMVSS 302
Flammability Classification				IEC 60695-11-10, -20
0.06 in (1.5 mm)	HB	--		
0.12 in (3.0 mm)	HB	--		
Glow Wire Flammability Index				IEC 60695-2-12
0.06 in (1.5 mm)	1200 (650)	--	°F (°C)	
0.12 in (3.0 mm)	1200 (650)	--	°F (°C)	
Glow Wire Ignition Temperature				IEC 60695-2-13
0.06 in (1.5 mm)	1290 (700)	--	°F (°C)	
0.12 in (3.0 mm)	1290 (700)	--	°F (°C)	


### Additional Information

- 1.) Not for use in food contact applications
- 2.) Not for use in medical or pharmaceutical applications

Technical Data Sheet

# SCHULAMID® 612 GF 50

Polyamide 612  
Engineering Plastics

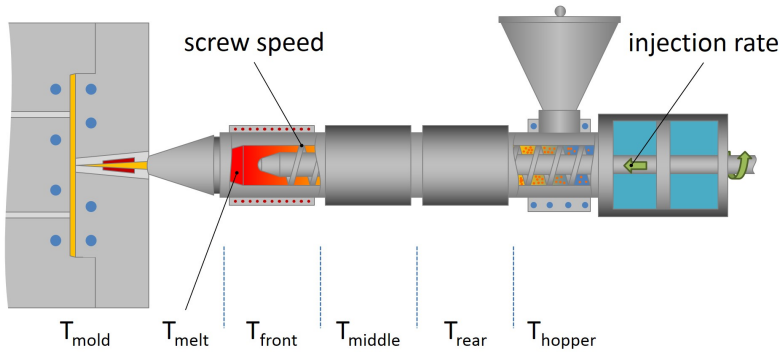

Injection	Dry (English)	Dry (SI)
Drying Temperature	176 °F	80 °C
Drying Time	3.0 to 4.0 hr	3.0 to 4.0 hr
Suggested Max Moisture	0.04 to 0.10 %	0.04 to 0.10 %
Suggested Max Regrind	20 %	20 %
Processing (Melt) Temp	464 to 536 °F	240 to 280 °C
Mold Temperature	122 to 194 °F	50 to 90 °C

**Notes**

<sup>1</sup> 0.079 in/min (2.0 mm/min)

**Notes**

These are typical property values not to be construed as specification limits.