

# Thermoplastic Polyurethane Elastomers (TPU)

Elastollan® –  
Product Range

 **BASF**

The Chemical Company



塑料数据专家 [www.ponci.com.cn/wxb/](http://www.ponci.com.cn/wxb/) +13538586433 +18816996168




# Contents

<b>Quality Management to DIN EN ISO 9001</b>	Page	<b>2</b>	
<b>Nomenclature for Elastollan</b>	Page	<b>3</b>	
<b>Packaging, Storage and Shelf live of Elastollan</b>	Page	<b>3</b>	
<b>Master-batches</b>	Page	<b>3</b>	
<b>Elastollan 1100 grades</b>	Based on Polyether-Polyurethane	Pages	<b>4 and 5</b>
<b>Elastollan 1200 grades</b>	Based on Polyether-Polyurethane	Pages	<b>6 and 7</b>
<b>Elastollan C grades</b>	Based on Polyester-Polyurethane	Pages	<b>8 and 9</b>
<b>Elastollan HPM grades</b>	Based on Polyester-Polyurethane	Pages	<b>10 and 11</b>
<b>Elastollan B grades</b>	Based on Polyester-Polyurethane	Pages	<b>12 and 13</b>
<b>Elastollan 600 and 800 grades</b>	Based on Polyester-Polyurethane, transparent	Pages	<b>14 and 15</b>
<b>Elastollan S grades</b>	Based on Polyester-Polyurethane	Pages	<b>16 and 17</b>
<b>Elastollan 500 grades</b>	Based on Polyester-Polyurethane	Pages	<b>18 and 19</b>
<b>Elastollan Aliphatic grades</b>	Aliphatic Polyurethane	Pages	<b>20 and 21</b>
<b>Elastollan R grades</b>	Glass fibre re-inforced Polyurethane	Pages	<b>22 and 23</b>
<b>Elastollan</b>	flame retardant	Pages	<b>24 and 25</b>
<b>Elastollan/Special products</b>	Polyether/Polyester-Polyurethane	Pages	<b>26 and 27</b>

## Quality Management

We are certified according to:  
ISO/TS 16949  
DIN EN ISO 9001  
DIN EN ISO 14001

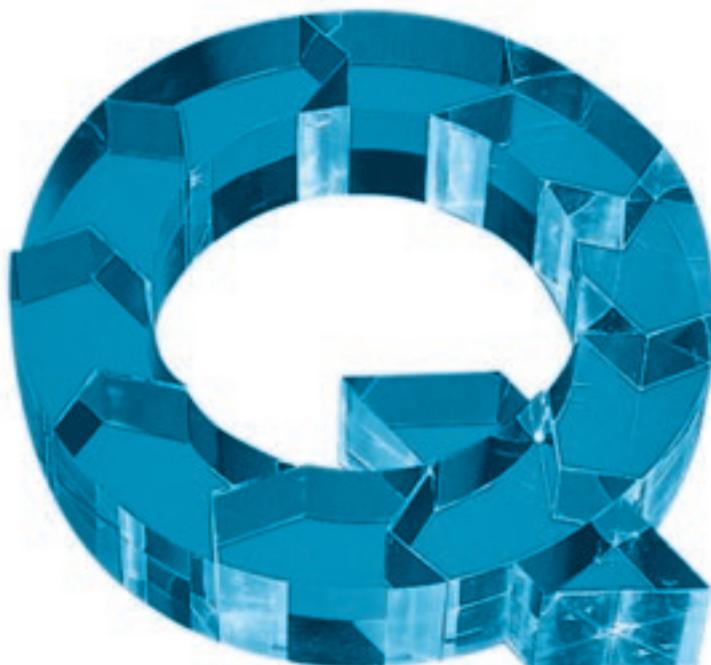

Edition: August 2013



## Nomenclature for Elastollan

Elastollan		11	85	A	10	W	000
<p><b>Elastollan</b> Elastollan is the registered trademark of BASF Polyurethanes GmbH for thermoplastic Polyurethane Elastomers.</p> <p>The product code consists of a letter and a number combination.</p> <p><b>Elastollan A and L stand for aliphatic thermoplastic thermoplastic Polyurethanes</b></p>	<p><b>Grade</b> The letter or number characterizes the basis polyol B, C, S, 5, 6, 7, 8 = Polyester 10, 11, 12 = Polyether R = glass-fibre reinforced grades LP = Laboratory product still in development SP = Special product, modified to meet customer's requirement N = based on renewable raw materials</p>	<p><b>Hardness</b> A = Shore A D = Shore D</p>	<p><b>Particle form</b> 1 = cylindrical or lentil shaped pellets 5 = diced</p>	<p><b>Lubricant</b> 0 = without lubricant 3, 5 = with lubricant</p>	<p><b>Additives</b> ESD = electronic sensitive devices FHF = flame retardant halogen free HPM = high performance material M = matt surface N = not stabilized U = UV stabilized P/W/WH = contains plasticiser T = approved for drinking water applications</p>	<p><b>Additives</b> 000 = natural colour 100 bis 999 = code for included additive</p>	

## Master-batches

Elastollan Konz and Elastollan Konz V are pigments and various additive master-batches. They can be used not only to colour, but also to improve processing and to improve stability against e.g. UV radiation, as blowing agent and for modification in various property areas.

Elastollan X-Flex are additives with crosslinking properties.

## Delivery form, Packing, Storage and Shelf-life

### Delivery form

Diced, Lentil or cylindrical shaped pellets.

### Packing for all Elastollan grades excluding R grades

- Multi Layer PE bag, 25kg net
- Oktabins with PE liner bags, ca. 1000kg net
- Big Bags, ca. 900kg net
- Tanker, ca. 20t net.

### Packing for R grades

- Sealed drums with PE liner bags, 125kg net
- Oktabins with PE liner bags, ca. 1000kg net
- Tanker, ca. 20t net.

### Storage and shelf-life

Approximately six months from delivery date in original sealed containers with cool dry storage.



# Elastollan 1100 grades

Thermoplastic Polyether Polyurethane Elastomers with outstanding hydrolysis resistance, low temperature flexibility and resistance to micro-organisms.

Physical Properties	Units	Test method	Elastollan					
			1170 A	1175 A W	1180 A	1185 A W	1185 A	1185 A M
Hardness	Shore A	DIN ISO 7619-1 (3s)	71	75	80	83	87	88
Hardness	Shore D	DIN ISO 7619-1 (3s)					36	39
Density	g/cm <sup>3</sup>	DIN EN ISO 1183-1-A	1,08	1,14	1,11	1,16	1,12	1,11
Tensile strength	MPa	DIN 53504-S2	30	40	45	40	45	45
Elongation at break	%	DIN 53504-S2	850	700	650	700	600	600
Stress at 20% elongation	MPa	DIN 53504-S2	1,3	2	2	2,5	2,5	3,5
Stress at 100% elongation	MPa	DIN 53504-S2	2	4	4,5	6	6	7
Stress at 300% elongation	MPa	DIN 53504-S2	4,8	8	8	8	10	12
Modulus of elasticity – tensile test	MPa	DIN EN ISO 527						
Tear strength	kN/m	DIN ISO 34-1Bb	44	40	55	50	70	60
Abrasion loss	mm <sup>3</sup>	DIN ISO 4649-A	<50	45	30	40	25	60
Compression set at room temperature, 72 h	%	DIN ISO 815	24	20	25	20	25	35
Compression set at 70°C, 24h	%	DIN ISO 815	50	40	45	35	45	45
Tensile strength after storage in water at 80°C for 42 days	MPa	DIN 53504-S2		28	30	30	32	30
Elongation at break after storage in water at 80°C for 42 days	%	DIN 53504-S2		750	700	700	600	650
Notched impact strength (Charpy) +23°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1		kJ/m <sup>2</sup>	kJ/m <sup>2</sup>	kJ/m <sup>2</sup>	kJ/m <sup>2</sup>	kJ/m <sup>2</sup>
Notched impact strength (Charpy) -30°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1		kJ/m <sup>2</sup>	kJ/m <sup>2</sup>	kJ/m <sup>2</sup>	kJ/m <sup>2</sup>	kJ/m <sup>2</sup>
Fire behaviour		UL 94		V0/V2 <sup>2)</sup>	HB	V2	HB	

<sup>1)</sup> Extrusion quality for pneumatic tubing

<sup>2)</sup> according to wall section

kB = no fracture

Certain 1100 grades are available in uv-stabilized versions.

## Typical applications

Cable jackets, plugs and terminations, spiral tubing, Films, ski-boot shells, ear tags, technical mouldings like mining screens, railway pads, seals.

## Processability

Processable by injection moulding, extrusion and blow moulding

Process temperature (injectin moulding): 170 to 240 °C

Mould temperature: 20 to 70 °C

Processing temperature (extrusion): 160 to 220 °C.



1185 A WM	1190 A	1195 A	1198 A <sup>1)</sup>	1154 D	1160 D	1164 D	1174 D			
87	92	96								
39	42	48	52	53	60	64	73			
1,13	1,14	1,15	1,16	1,17	1,18	1,18	1,20			
30	50	55	50	50	50	50	50			
650	550	500	450	450	400	350	300			
4	4,5	6	9	11	13	16	25			
7	8,5	10	15	17	19	25	30			
10	16	18	28	38	41	45	45			
				150	200	250	560			
55	85	100	125	150	170	190	220			
65	25	25	25	20	20	20	20			
25	25	30	35	40	40	40	50			
43	45	45	50	50	50	50	55			
30	35	37	35	35	35	35	35			
600	600	500	450	450	450	400	400			
kB kB	kB kB	kB kB	kB 190	kB 18	kB 16	kB 12	kB 5			
			HB							

#### Please note

The stated values for individual grades are typical test results and not limiting specification values.

Quoted results are from measurements on injection moulded test platens, post tempered for 20 h at 100 °C.

#### Specialist application areas

Please contact our technical department for further regulatory information and approvals in the case of food contact, drinking water or medical applications.



# Elastollan 1200 grades

Highly transparent thermoplastic Polyether Polyurethane Elastomer with good hydrolysis resistance, low temperature flexibility and resistance to micro-organismus

Physical Properties	Units	Test method	Elastollan 1298 A U	1254 D U	1260 D U	1264 D U
Hardness	Shore D	DIN ISO 7619-1 (3s)	50	57	61	64
Density	g/cm <sup>3</sup>	DIN EN ISO 1183-1-A	1,16	1,17	1,2	1,2
Tensile strength	MPa	DIN 53504-S2	60	60	45	50
Elongation at break	%	DIN 53504-S2	460	470	350	350
Stress at 20% elongation	MPa	DIN 53504-S2	9	16,5	15	17
Stress at 100% elongation	MPa	DIN 53504-S2	16	23	22,5	25
Stress at 300% elongation	MPa	DIN 53504-S2	28	35	36,5	35
Modulus of elasticity – tensile test	MPa	DIN EN ISO 52-7	90	180	225	330
Tear strength	kN/m	DIN ISO 34-1Bb	130	165	165	170
Abrasion loss	mm <sup>3</sup>	DIN ISO 4649-A	25	30	40	40
Compression set at room temperature, 72h	%	DIN ISO 815	28	42	45	48
Compression set at 70°C, 24h	%	DIN ISO 815	45	54	52	48
Tensile strength after storage in water at 80°C for 42 days	MPa	DIN 53504-S2	50	53	51	46
Elongation at break after storage in water at 80°C for 42 days	%	DIN 53504-S2	550	520	500	450
Notched impact strength (Charpy) +23°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1	kB	kB	kB	kB
Notched impact strength (Charpy) - 30°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1	171	14	13	11,5

*kB = no fracture*

## Typical applications

Ski boot shells, ski components, Films.

## Processability

Processable by injection moulding as well as by extrusion

Process temperature (injection moulding): 215 to 240 °C

Mould temperature: 20 to 70 °C

Process temperature (extrusion): 200 to 230 °C.



### **Please note**

The stated values for individual grades are typical test results and not limiting specification values.

Quoted results are from measurements on injection moulded test platens, post tempered for 20 h at 100 °C.

## Specialist application areas

Please contact our technical department for further regulatory information and approvals in the case of food contact, drinking water or medical applications.



## Elastollan C grades

Thermoplastic Polyester Polyurethane Elastomers with excellent mechanical properties. Outstanding tensile strength and high elongation at break, good damping characteristics, a high resilience performance and very good wear resistance.

Physical Properties	Units	Test method	Elastollan C 60 AP	C 78 A	C 80 A	C 85 A	C 88 A <sup>1)</sup>
Hardness	Shore A	DIN ISO 7619-1 (3s)	60	80	82	87	88
Hardness	Shore D	DIN ISO 7619-1 (3s)				36	37
Density	g/cm <sup>3</sup>	DIN EN ISO 1183-1-A	1,15	1,18	1,19	1,19	1,19
Tensile strength	MPa	DIN 53504-S2	38	50	50	50	50
Elongation at break	%	DIN 53504-S2	1000	650	650	650	600
Stress at 20% elongation	MPa	DIN 53504-S2	1	2	2,5	3	3,5
Stress at 100% elongation	MPa	DIN 53504-S2	2,4	4	4,5	5,5	6
Stress at 300% elongation	MPa	DIN 53504-S2	5	7,5	8,5	9,5	13
Modulus of elasticity – tensile test	MPa	DIN EN ISO 527					
Tear strength	kN/m	DIN ISO 34-1Bb	40	60	65	70	75
Abrasion loss	mm <sup>3</sup>	DIN ISO 4649-A	50	30	30	30	30
Compression set at room temperature, 72 h	%	DIN ISO 815	21	25	25	25	25
Compression set at 70°C, 24h	%	DIN ISO 815	37	35	35	35	40
Tensile strength after storage in water for 21 days at 80°C	MPa	DIN 53504-S2		35	35	38	38
Elongation at break after storage in water for 21 days at 80°C	%	DIN 53504-S2		650	650	650	650
Notched impact strength (Charpy) +23°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1		kJB	kJB	kJB	kJB
Notched impact strength (Charpy) - 30°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1		kJB	kJB	kJB	kJB
Fire behaviour		UL 94				HB	

<sup>1)</sup> Extrusion quality for round belts

<sup>2)</sup> Extrusion quality for pneumatic tubing

kJB = no fracture

### Typical applications

Spiral tubing, pneumatic tubing, round belting, technical mouldings e.g. bushes, dust caps, seals, joints, blow moulded bellows, fan belts.

### Processability

Processable by injection moulding, extrusion and blow moulding

Process temperature (injection moulding): 170 to 240 °C

Mould temperature: 20 to 70 °C

Process temperature (extrusion): 150 to 230 °C.



C 90 A	C 95 A	C 98 A <sup>2)</sup>	C 59 D	C 60 D	C 64 D	C 74 D		
93	96							
41	47	52	57	60	63	73		
1,20	1,21	1,22	1,23	1,23	1,24	1,25		
55	55	50	50	50	45	45		
550	550	550	500	450	400	350		
7	8	11	12	16	17	28		
9	11	14	17	20	24	30		
15	22	26	30	35	35	35		
		160	250	330	390	730		
95	120	130	160	180	200	240		
25	25	30	20	20	20	20		
25	30	30	30	40	40	40		
40	45	50	50	50	55	60		
40	40	40	43	43	43	45		
550	500	550	480	450	420	380		
kB kB	kB kB	kB 25	kB 12	kB 8	kB 7	120 4		
	HB	HB	HB			HB		


#### Please note

The stated values for individual grades are typical test results and not limiting specification values.

Quoted results are from measurements on injection moulded test platens, post tempered for 20 h at 100 °C.

#### Specialist application areas

Please contact our technical department for further regulatory information and approvals in the case of food contact, drinking water or medical applications.



# Elastollan HPM grades

Thermoplastic Polyester Polyurethane Elastomers with excellent mechanical properties, very good damping and resilience performance, heat resistance and improved cycle times.

Physical Properties	Units	Test method	Elastollan C 60 A HPM	C 65 A HPM	C 70 A HPM	C 75 A HPM
Hardness	Shore A	DIN ISO 7619-1 (3s)	63	67	71	75
Hardness	Shore D	DIN ISO 7619-1 (3s)				
Density	g/cm <sup>3</sup>	DIN EN ISO 1183-1-A	1,17	1,18	1,18	1,18
Tensile strength	MPa	DIN 53504-S2	35	37	40	40
Elongation at break	%	DIN 53504-S2	1000	950	900	900
Stress at 20% elongation	MPa	DIN 53504-S2	0,85	1,5	1,5	2
Stress at 100% elongation	MPa	DIN 53504-S2	1,5	2,0	2,5	3,5
Stress at 300% elongation	MPa	DIN 53504-S2	2	4,0	4,5	6
Tear strength	kN/m	DIN ISO 34-1Bb	40	44	45	50
Abrasion loss	mm <sup>3</sup>	DIN ISO 4649-A	55	55	50	50
Compression set at room temperature, 72h	%	DIN ISO 815	25	25	25	25
Compression set at 70°C, 24h	%	DIN ISO 815	43	37	35	35
Compression set at 100°C, 24h	%	DIN ISO 815	60	55	50	50
Tensile strength after storage in water for 21 days at 80°C	MPa	DIN 53504-S2	20	25	30	35
Elongation at break after storage in water for 21 days at 80°C	%	DIN 53504-S2	1100	900	850	800
Notched impact strength (Charpy) +23°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1	kB	kB	kB	kB
Notched impact strength (Charpy) - 30°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1	kB	kB	kB	kB
Vicat-softening temperature A 120°C/h	°C	DIN EN ISO 306	70	80	90	100

*kB = no fracture*

## Typical applications

(Automotive)  
e.g. sealings, stop dampers, cable jackets.

## Processability

Processable by injection moulding, extrusion and blow moulding

Process temperature (injection moulding): 190 to 220 °C

Mould temperature: 20 to 50 °C

Process temperature (extrusion): 180 to 230 °C.



C 85 A HPM	785 A HPM	754 D HPM					
85	85						
		55					
1,20	1,18	1,24					
45	45	35					
750	700	450					
3,5	3,5	15					
6,0	6	20					
11	11	40					
70	70	160					
40	40	20					
20	20	25					
30	30	35					
45	45	45					
35	40	30					
800	750	550					
kB kB	kB kB	n. b. n. b.					
120	120	155					

#### Please note

The stated values for individual grades are typical test results and not limiting specification values.

Quoted results are from measurements on injection moulded test platens, post tempered for 20 h at 100 °C.

#### Specialist application areas

Please contact our technical department for further regulatory information and approvals in the case of food contact, drinking water or medical applications.



## Elastollan B grades

Thermoplastic Polyester Polyurethane Elastomers with excellent mechanical properties, outstanding wear resistance, good tensile strength, good damping and resilience performance and superior low temperature flexibility.

Physical Properties	Units	Test method	Elastollan B 60 AWH TSG	B 60 A ESD <sup>1),2)</sup>	B 60 A ESD M <sup>1)</sup>	B 80 A
Hardness	Shore A	DIN ISO 7619-1 (3s)	60	63	63	82
Hardness	Shore D	DIN ISO 7619-1 (3s)				
Density	g/cm <sup>3</sup>	DIN EN ISO 1183-1-A	1,18	1,17	1,17	1,19
Tensile strength	MPa	DIN 53504-S2	25	30	30	50
Elongation at break	%	DIN 53504-S2	800	800	800	600
Stress at 20 % elongation	MPa	DIN 53504-S2	1	1	1	2
Stress at 100 % elongation	MPa	DIN 53504-S2	2,5	2,5	2,5	5
Stress at 300 % elongation	MPa	DIN 53504-S2	6,5	6,5	6,5	14,5
Modulus of elasticity – tensile test	MPa	DIN EN ISO 527				
Tear strength	kN/m	DIN ISO 34-1Bb	40	50	50	85
Abrasion loss	mm <sup>3</sup>	DIN ISO 4649-A	100	60	60	35
Compression set at room temperature, 72h	%	DIN ISO 815	25	20	20	20
Compression set at 70°C, 24h	%	DIN ISO 815	40	30	30	30
Tensile strength after storage in water at 80°C for 21 days	MPa	DIN 53504-S2		25	25	40
Elongation at break after storage in water at 80°C for 21 days	%	DIN 53504-S2		900	900	600
Notched impact strength (Charpy) +23°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1	kB	kB	kB	kB
Notched impact strength (Charpy) - 30°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1	kB	kB	kB	kB
Specific volume resistivity	Ohm x cm	IEC60093		5x10 <sup>7</sup>	5x10 <sup>7</sup>	

Certain UV stabilised B grades are available on request

- 1) for safety shoes
- 2) transparent

### Typical applications

Sport-shoe soles and accessories, Skiboot shells, technical mouldings, e.g. seals, castor tyres, tubing.

### Processability

Processable by injection moulding, extrusion and blow moulding

Process temperature (injection moulding): 190 to 220 °C

Mould temperature: 20 to 50 °C

Process temperature (extrusion): 180 to 230 °C.



B 85 A	B 90 A	B 95 A	B 98 A	B 60 D	B 64 D		
83	91	96					
	42	48	50	60	64		
1,20	1,21	1,22	1,22	1,23	1,24		
55	55	55	55	55	55		
600	550	550	500	500	450		
2	4	7	8	13	17		
4	7	10	12	16	19		
15	20	22	30	30	35		
			140	240	320		
75	90	100	130	150	180		
35	30	30	25	25	25		
25	25	30	35	35	35		
35	40	40	45	45	50		
40	40	40	40	40	40		
600	550	500	500	450	400		
kB kB	kB kB	kB 200	kB 18	kB 10	kB 8		

### Please note

The stated values for individual grades are typical test results and not limiting specification values.

Quoted results are from measurements on injection moulded test platens, post tempered for 20 h at 100 °C.

## Specialist application areas

Please contact our technical department for further regulatory information and approvals in the case of food contact, drinking water or medical applications.



# Elastollan 600 and 800 grades

Transparent, Thermoplastic Polyester Polyurethane Elastomers with excellent mechanical properties, outstanding wear resistance, good damping and resilience performance.

Physical Properties	Units	Test method	Elastollan 670 AWHU	685 A	690 A	695 A
Hardness	Shore A	DIN ISO 7619-1 (3s)	70	86	90	
Hardness	Shore D	DIN ISO 7619-1 (3s)				50
Density	g/cm <sup>3</sup>	DIN EN ISO 1183-1-A	1,19	1,21	1,21	1,22
Tensile strength	MPa	DIN 53504-S2	35	50	50	50
Elongation at break	%	DIN 53504-S2	650	600	550	500
Stress at 20% elongation	MPa	DIN 53504-S2	1	2,8	4	6
Stress at 100% elongation	MPa	DIN 53504-S2	3	5,5	7	10
Stress at 300% elongation	MPa	DIN 53504-S2				
Tear strength	kN/m	DIN ISO 34-1Bb	40	75	85	100
Abrasion loss	mm <sup>3</sup>	DIN ISO 4649-A	40	40	40	40
Compression set at room temperature, 72h	%	DIN ISO 815	25	25	25	25
Compression set at 70°C, 24h	%	DIN ISO 815	40	45	45	40
Tensile strength after storage in water at 80°C for 21 days	MPa	DIN 53504-S2	30	40	40	40
Elongation at break after storage in water at 80°C for 21 days	%	DIN 53504-S2	700	650	600	550
Notched impact strength +23°C Notched impact strength -30°C	kJ/m <sup>2</sup> kJ/m <sup>2</sup>	DIN EN ISO 179-1 DIN EN ISO 179-1	kB kB	kB kB	kB kB	kB 200

Materials in the 600 series are available with UV stabilisation

*kB = no fracture*

## Typical applications

Decorative parts and damping elements for the sport shoe industry, Ski tips, tubes and Films.

## Processability

Processable by injection moulding, extrusion and blow moulding

Process temperature (injection moulding): 175 to 230 °C

Mould temperature: 20 to 50 °C

Process temperature (extrusion): 175 to 220 °C.



### **Please note**

The stated values for individual grades are typical test results and not limiting specification values.

Quoted results are from measurements on injection moulded test platens, post tempered for 20h at 100°C.

## Specialist application areas

Please contact our technical department for further regulatory information and approvals in the case of food contact, drinking water or medical applications.



## Elastollan S grades

Thermoplastic Polyester Polyurethane Elastomers with excellent mechanical properties, outstanding wear resistance, good damping and resilience performance and excellent tear strength.

Physical Properties	Units	Test method	Elastollan S 60 AP	S 70 A	S 80 A	S 85 A
Hardness	Shore A	DIN ISO 7619-1 (3s)	63	70	81	85
Hardness	Shore D	DIN ISO 7619-1 (3s)				
Density	g/cm <sup>3</sup>	DIN EN ISO 1183-1-A	1,19	1,22	1,22	1,23
Tensile strength	MPa	DIN 53504-S2	35	34	50	55
Elongation at break	%	DIN 53504-S2	750	720	750	650
Stress at 20% elongation	MPa	DIN 53504-S2	1	1	2	2
Stress at 100% elongation	MPa	DIN 53504-S2	3	3	4	5
Stress at 300% elongation	MPa	DIN 53504-S2	6,5	5	8	8
Modulus of elasticity – tensile test	MPa	DIN EN ISO 527				
Tear strength	kN/m	DIN ISO 34-1Bb	45	55	60	70
Abrasion loss	mm <sup>3</sup>	DIN ISO 4649-A	35	42	40	35
Compression set at room temperature, 72 h	%	DIN ISO 815			25	25
Compression set at 70 °C, 24 h	%	DIN ISO 815			35	35
Notched impact strength (Charpy) +23°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1			kJ	kJ
Notched impact strength (Charpy) - 30°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1			kJ	kJ
Fire behaviour		UL 94				

*kB = no fracture*

### Typical applications

Shoe soles, top pieces, tubes, technical parts e.g. castor tyres.

### Processability

Processable by injection moulding, extrusion and blow moulding

Process temperature (injection moulding): 175 to 240 °C

Mould temperature: 20 to 70 °C

Process temperature (extrusion): 175 to 220 °C.



S 90 A	S 95 A	S 98 A	S 60 D	S 64 D				
93	96							
41	48	55	60	64				
1,24	1,24	1,25	1,25	1,26				
55	50	45	45	45				
600	550	500	500	450				
6	8	13	15	22				
9	11	16	18	23				
13	20	23	34	38				
		200	250	410				
95	120	150	170	200				
30	30	25	25	25				
25	25	30	40	45				
45	45	45	50	55				
kB kB	kB 14	kB 13	kB 4	140 4				
HB								

#### Please note

The stated values for individual grades are typical test results and not limiting specification values.

Quoted results are from measurements on injection moulded test platens, post tempered for 20h at 100°C.

#### Specialist application areas

Please contact our technical department for further regulatory information and approvals in the case of food contact, drinking water or medical applications.



## Elastollan 500 grades

Thermoplastic Polyester Polyurethane Elastomers with excellent mechanical properties and in particular, good abrasion resistance.

## Typical applications

Shoes, parts subject to regular wear and tear, castor tyres and films.

## Processability

Processable by injection moulding, and extrusion

Process temperature (injection moulding): 175 to 230 °C

Mould temperature: 20 to 70 °C

Process temperature (extrusion):  
175 to 220°C.



### **Please note**

The stated values for individual grades are typical test results and not limiting specification values.

Quoted results are from measurements on injection moulded test platens, post tempered for 20 h at 100 °C.

## Specialist application areas

Please contact our technical department for further regulatory information and approvals in the case of food contact, drinking water or medical applications.



## **Elastollan Aliphatic grades**

Aliphatic, thermoplastic Polyurethane with excellent colour fastness, good flow characteristics, detailed reproduction of surface structures, resistance to hydrolysis and low fogging values.

## Typical applications

Applications in the automotive interior, e.g. inner door handles, instrument panels, cover centre consoles, lever wheels, slider covers, tubes, films.

## Processability

Processable by injection moulding,  
extrusion and slush moulding

Process temperature (injection moulding): 190 to 235 °C

Process temperature (extrusion):  
180 to 230 °C

Mould temperature: 20 to 60 °C.



### **Please note**

The stated values for individual grades are typical test results and not limiting specification values.

Quoted results are from measurements on injection moulded test platens, post tempered for 20 h at 100 °C.

## Specialist application areas

Please contact our technical department for further regulatory information and approvals in the case of food contact, drinking water or medical applications.



## Elastollan Typreihe R

Glass fibre reinforced thermoplastic Polyester Polyurethane Elastomers with excellent mechanical properties, outstanding impact strength, high stiffness whilst maintaining good elongation, low coefficient of expansion similar to Aluminium, low shrinkage, good paintability.

Physical Properties	Units	Test method	Elastollan R 1001	R 1000	R 2000	R 3000
Modulus of elasticity – tensile test	MPa	DIN EN ISO 527	350	1000	2000	2800
Density	g/cm <sup>3</sup>	DIN EN ISO 1183-1-A	1,27	1,36	1,37	1,38
Hardness	Shore D	DIN ISO 7619-1 (3s)	50	60	67	73
Glass-fibre content	%		10	20	20	20
Tensile strength (test specimen type 1A) strain rate at 50mm/min	MPa	DIN EN ISO 527	30	50	65	80
Elongation at break (test specimen type 1A) strain rate at 50mm/min	%	DIN EN ISO 527	65	40	25	10
Impact strength (Charpy) + 23°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1	kB*	kB*	140	120
Impact strength (Charpy) - 30°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1	160	130	110	70
Notched impact strength (Charpy) + 23°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1	70	70	50	30
Notched impact strength (Charpy) - 30°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1	30	20	10	10
Deflection temperature	°C	DIN EN ISO 75-2/A	65	90	115	120
Deflection temperature	°C	DIN EN ISO 75-2/B	125	120	138	155
Coefficient of linear expansion between 23 °C and 80 °C	10 <sup>-6</sup> · K <sup>-1</sup>	DIN 53752-A	28	20	20	20
Colour			natural	natural	natural	natural
Fire behaviour		UL 94				HB

### Typical applications

Automotive body and panels and structural door trim parts, under body sealants, technical mouldings e.g. plugs, ski tips.

### Processability

Processable by injection moulding  
Process temperature (injection moulding): 225 to 245 °C  
Process temperature: 50 to 70 °C.



R 3001	R 6000							
3000	6400							
1,32	1,40							
75	n. b.							
15	26							
65	115							
25	7							
100 70	84 67							
30 6	21 12							
110 155								
30								
black	natural							

#### Please note

The stated values for individual grades are typical test results and not limiting specification values.

Quoted results are from measurements on injection moulded test platens, post tempered for 20 h at 100 °C.

#### Specialist application areas

Please contact our technical department for further regulatory information and approvals in the case of food contact, drinking water or medical applications.



# Elastollan/flame retardant grades

Thermoplastic Polyether Polyurethane special products,  
halogenfree flame retardant.

Physical Properties	Units	Test method	Elastollan 1177 A FHF	1185 A FHF	1190 A FHF	1191 A FHF
Hardness	Shore A	DIN ISO 7619-1 (3s)	77	89	90	91
Hardness	Shore D	DIN ISO 7619-1 (3s)		37		
Density	g/cm <sup>3</sup>	DIN EN ISO 1183-1-A	1,2	1,23	1,25	1,26
Tensile strength	MPa	DIN 53504-S2	22	35	25	24
Elongation at break	%	DIN 53504-S2	800	600	550	550
Stress at 20% elongation	MPa	DIN 53504-S2	2	3,5	4,8	4,8
Stress at 100% elongation	MPa	DIN 53504-S2	3	8	8,4	8,5
Stress at 300% elongation	MPa	DIN 53504-S2	5	13	10,5	11,6
Modulus of elasticity – tensile test	MPa	DIN EN ISO 527				
Tear resistance	kN/m	DIN ISO 34-1Bb	53	60	60	60
Abrasion loss	mm <sup>3</sup>	DIN ISO 4649-A	75	35	30	40
Compression set at room temperature, 72 h	%	DIN EN ISO 815		25	26	24
Compression set at 70°C, 24 h	%	DIN EN ISO 815		45	43	43
Notched impact strength (Charpy) +23°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1		kb	kb	
Notched impact strength (Charpy) -30°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1		120	46	
Tensile strength after storage in water at 80°C for 42 days	MPa	DIN 53504-S2		20	15	
Elongation at break after storage in water at 80°C for 42 days	%	DIN 53504-S2		600	640	
Fire behaviour		UL 94		V0	V0	

<sup>1)</sup> according to wall section

## Typical applications

Cable jackets, Films

## Processability

Processable by extrusion

Process temperature: 175 to 220 °C.



1147 D FHF	1154 D FHF	1185 A HFFR						
94		86						
48	58							
1,29	1,27	1,42						
13	30	20						
400	400	580						
7	13	3,6						
9	19	6						
10	33	7,8						
	160							
60	110	55						
60	30							
38	30							
50	45							
kB 21	50 3							
7	20	12						
270	400	750						
	V0/V2 <sup>1)</sup>							

#### Please note

The stated values for individual grades are typical test results and not limiting specification values.

Quoted results are from measurements on injection moulded test platens, post tempered for 20h at 100°C.

#### Specialist application areas

Please contact our technical department for further regulatory information and approvals in the case of food contact, drinking water or medical applications.



# Elastollan/Special products

Thermoplastic Polyether and Polyester Polyurethane Special products with excellent mechanical properties, outstanding wear resistance, good damping and resilience performance and excellent tear strength.

Physical Properties	Units	Test method	Elastollan	1085 A	Soft 35 AP <sup>1)</sup>	Soft 45 AP <sup>2)</sup>
			1075 AU	Ether based alternative	Ester based	Ester based
Hardness	Shore A	DIN ISO 7619-1 (3s)	78	87	40	50
Hardness	Shore D	DIN ISO 7619-1 (3s)				
Density	g/cm <sup>3</sup>	DIN EN ISO 1183-1-A	1,13	1,15	1,18	1,18
Tensile strength	MPa	DIN 53504-S2	15	35	12	34
Elongation at break	%	DIN 53504-S2	900	700	1150	950
Stress at 20 % elongation	MPa	DIN 53504-S2	2	4,8	0,5	0,6
Stress at 100 % elongation	MPa	DIN 53504-S2	4,6	7,3	1	1,5
Stress at 300 % elongation	MPa	DIN 53504-S2	7,8	16,5	2,5	3
Tear resistance	kN/m	DIN ISO 34-1Bb	30	55	27	42
Abrasion	mm <sup>3</sup>	DIN ISO 4649-A	200	50	165	39
Compression set at room temperature, 72 h	%	DIN EN ISO 815	20	22		34
Compression set at 70°C, 24 h	%	DIN EN ISO 815	35	34		53
Notched impact strength (Charpy) +23°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1	kJ/m <sup>2</sup>	kJ/m <sup>2</sup>		
Notched impact strength (Charpy) -30°C	kJ/m <sup>2</sup>	DIN EN ISO 179-1	kJ/m <sup>2</sup>	kJ/m <sup>2</sup>		

<sup>1)</sup> Suitable for foaming

## Typical applications

## Processability

<sup>2)</sup> Available as ESD-version

Application specific formulations.

Processable by injection moulding and extrusion

kB = no fracture

Process temperature (injection moulding): 175 to 240 °C

Mould temperature: 20 to 70 °C

Process temperature (extrusion): 175 to 220 °C.



SP 806 Ether based for opaque films	SP 883 Ester based for opaque films	1385 A water vapour per- meable							
87	85	85							
1,12	1,19	1,21							
45	40	30							
550	550	750							
2,5	2	2,5							
6	5	4,6							
11,5	10,5								
60	60	45							
30	40	50							
26	22	26							
43	37	46							
kB kB	kB kB	kB kB							

#### Please note

The stated values for individual grades are typical test results and not limiting specification values.

Quoted results are from measurements on injection moulded test platens, post tempered for 20 h at 100 °C.

#### Specialist application areas

Please contact our technical department for further regulatory information and approvals in the case of food contact, drinking water or medical applications.



## Competence in Polyurethanes

With top quality products, a reputation for good customer service and continuous progress and development, Elastollan has secured a firm position in numerous markets.

We want to share our know how and experience to contribute to your own success: The versatile Elastollan is the ideal material to fulfill your requirements.

For further information, the following detailed brochures are available on request:

- Thermoplastic Polyurethane Elastomers: Elastollan
- Elastollan – Materialproperties
- Elastollan – Processing Recommendations
- Elastollan – Hinweise
- Elastollan – Electrical Properties
- Elastollan – Chemical Resistance

