

VECTRA® A530

Liquid Crystal Polymer

Best overall surface appearance with properties similar to A130. Less abrasive than glass fiber reinforced grades. Improved toughness over A130. Outstanding hydrolytic stability. Recommended where aesthetics are key. 30% mineral filled. Chemical abbreviation according to ISO 1043-1 : LCP Inherently flame retardant UL-Listing V-0 in natural and black at 0.38mm thickness per UL 94 flame testing, and UL-5VA in natural at 3.0mm. Relative-Temperature-Index (RTI) according to UL 746B: electrical 130°C, mechanical 130°C. UL = Underwriters Laboratories (USA)

Product information

Resin Identification	LCP-MD30 ^[OT, 1]	ISO 1043
Part Marking Code	>LCP-MD30< ^[OT, 1]	ISO 11469
[OT]: One time tested		
[1]: ISO 1043 declaration was adjusted to be consistent with IMDS entry for Vectra A530		

Rheological properties

Moulding shrinkage, parallel	0.2 %	ISO 294-4, 2577
Moulding shrinkage, normal	0.7 %	ISO 294-4, 2577

Typical mechanical properties

Tensile modulus	11000 MPa	ISO 527-1/-2
Tensile stress at break, 5mm/min	140 MPa	ISO 527-1/-2
Tensile strain at break, 5mm/min	3.7 ^[C, 2] %	ISO 527-1/-2
Flexural modulus	11100 ^[C, 2] MPa	ISO 178
Flexural strength	170 MPa	ISO 178
Compressive modulus	9500 MPa	ISO 604
Compressive stress at 1% strain	60 MPa	ISO 604
Charpy impact strength, 23°C	50 kJ/m ²	ISO 179/1eU
Charpy notched impact strength, 23°C	25 kJ/m ²	ISO 179/1eA
Izod notched impact strength, 23°C	27 kJ/m ²	ISO 180/1A
Izod impact strength, 23°C	40 kJ/m ²	ISO 180/1U
Hardness, Rockwell, M-scale	67	ISO 2039-2
Poisson's ratio	0.34 ^[C]	

[C]: Calculated

[2]: Statistical analysis; data harmonized for Vectra A530 nat/black & MT1345 nat

Thermal properties

Melting temperature, 10°C/min	280 °C	ISO 11357-1/-3
Temperature of deflection under load, 1.8 MPa	190 °C	ISO 75-1/-2
Temperature of deflection under load, 0.45 MPa	203 °C	ISO 75-1/-2
Temperature of deflection under load, 8 MPa	121 °C	ISO 75-1/-2
Vicat softening temperature, 50°C/h 50N	151 °C	ISO 306
Coefficient of linear thermal expansion (CLTE), parallel	13 E-6/K	ISO 11359-1/-2
Coefficient of linear thermal expansion (CLTE), normal	77 E-6/K	ISO 11359-1/-2

VECTRA® A530

Liquid Crystal Polymer

Flammability

Burning Behav. at thickness h	V-0 class	IEC 60695-11-10
-------------------------------	-----------	-----------------

Electrical properties

Relative permittivity, 100Hz	3.8	IEC 62631-2-1
Relative permittivity, 1MHz	3.2	IEC 62631-2-1
Dissipation factor, 100Hz	100 E-4	IEC 62631-2-1
Dissipation factor, 1MHz	160 E-4	IEC 62631-2-1
Volume resistivity	1E12 Ohm.m	IEC 62631-3-1
Surface resistivity	>1E15 Ohm	IEC 62631-3-2
Electric strength	44 kV/mm	IEC 60243-1
Comparative tracking index	200	IEC 60112
Arc Resistance	180 s	UL 746B

Physical/Other properties

Density	1650 kg/m³	ISO 1183
---------	------------	----------

Injection

Drying Recommended	yes
Drying Temperature	150 °C
Drying Time, Dehumidified Dryer	4 - 6 h
Processing Moisture Content	≤0.01 %
Melt Temperature Optimum	290 °C
Min. melt temperature	285 °C
Max. melt temperature	295 °C
Screw tangential speed	0.2 - 0.3 m/s
Mold Temperature Optimum	100 °C
Min. mould temperature	80 °C
Max. mould temperature	120 °C
Back pressure	3 MPa
Ejection temperature	227 °C

Characteristics

Processing	Injection Moulding
Delivery form	Pellets
Additives	Mineral Filler
Special characteristics	Light stabilised or stable to light, Specialty appearance, Hydrolysis resistant, High Flow

Additional information

Injection molding

Preprocessing

Vectra resins are well known for their excellent thermal and hydrolytic stability. In order to ensure these properties are optimum, the resin should be dried correctly prior to processing. Vectra A-grades should be dried at 150 C for a minimum of 4 hours in a desiccant dryer.

VECTRA® A530

Liquid Crystal Polymer

Processing

A three-zone screw evenly divided into feed, compression, and metering zones is preferred. A higher percentage of feed flights may be needed for smaller machines: 1/2 feed, 1/4 compression, 1/4 metering.

Vectra LCPs are shear thinning, their melt viscosity decreases quickly as shear rate increases. For parts that are difficult to fill, the molder can increase the injection velocity to improve melt flow.

Processing Notes

Pre-Drying

VECTRA should in principle be predried. Because of the necessary low maximum residual moisture content the use of dry air dryers is recommended. The dew point should be $\leq -40^{\circ}\text{C}$. The time between drying and processing should be as short as possible.


Storage

For subsequent storage of the material in the dryer until processed the temperature does not need to be lowered for grades A, B, C, D and V ($\leq 24\text{ h}$).

VECTRA® A530

Liquid Crystal Polymer

Stress-strain

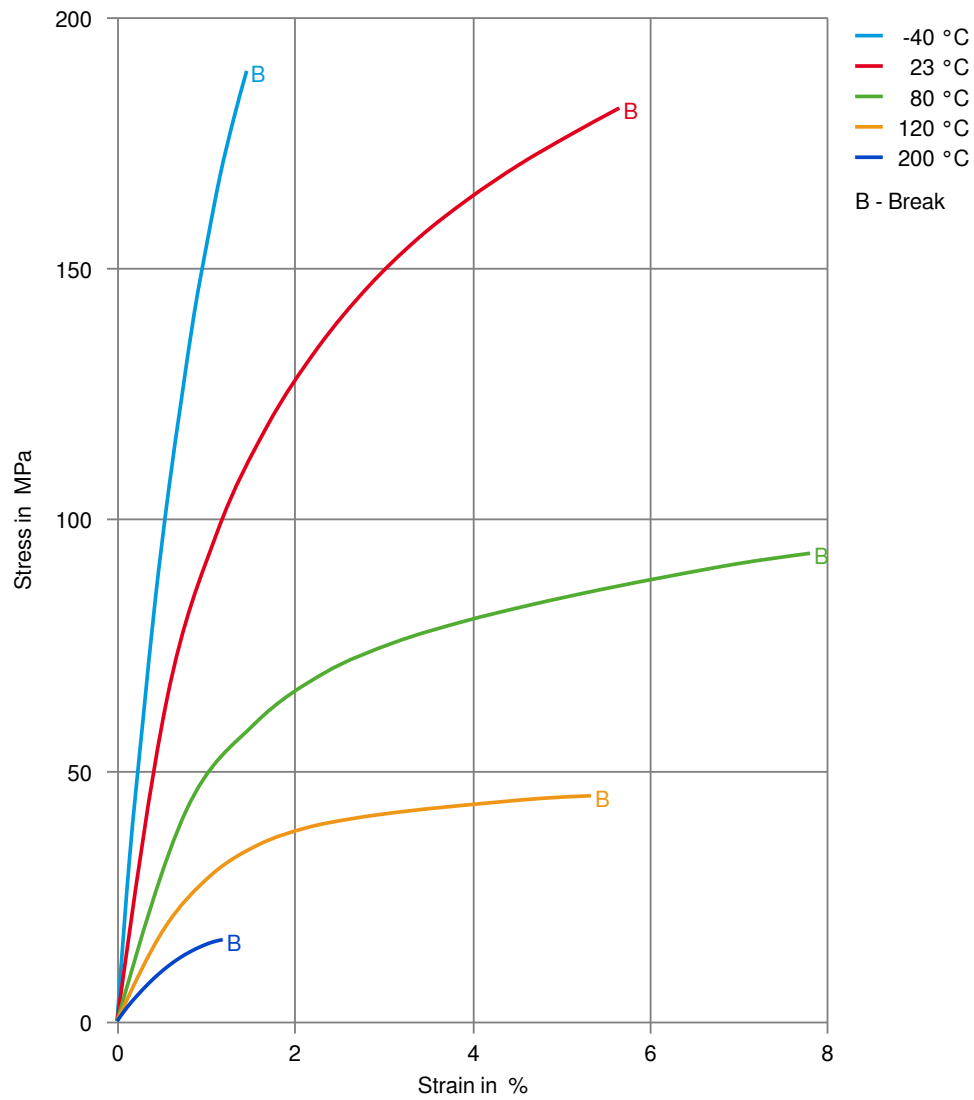

VECTRA® A530

Liquid Crystal Polymer

Secant modulus-strain

