

Durethan® BC30 000000
PA6-I

Envalior

Injection Molding, Unreinforced, Improved Impact

ISO 1043 PA6-I

Rheological properties	dry / cond	Unit	Test Standard
ISO Data			
Melt volume-flow rate, MVR	36 / *	cm ³ /10min	ISO 1133
Temperature	270 / *	°C	-
Load	2.16 / *	kg	-
Molding shrinkage, parallel	1.6 / *	%	ISO 294-4, 2577
Molding shrinkage, normal	1.8 / *	%	ISO 294-4, 2577

Mechanical Properties	dry / cond	Unit	Test Standard
ISO Data			
Tensile Modulus	2800 / 1200	MPa	ISO 527
Yield stress	65 / 40	MPa	ISO 527
Yield strain	4 / 20	%	ISO 527
Nominal strain at break	- / >50	%	ISO 527
Impact Strength (Charpy), +23°C	no break / no break	kJ/m ²	ISO 179/1eU
Impact Strength (Charpy), -30°C	no break / no break	kJ/m ²	ISO 179/1eU
Notched Impact Strength (Charpy), +23°C	10 / 50	kJ/m ²	ISO 179/1eA
Notched Impact Strength (Charpy), -30°C	- / 10	kJ/m ²	ISO 179/1eA
Puncture - maximum force, +23°C	4340 / 470	N	ISO 6603-2
Puncture - maximum force, -30°C	5870 / 940	N	ISO 6603-2
Puncture energy, +23°C	55 / 140	J	ISO 6603-2
Puncture energy, -30°C	65 / 20	J	ISO 6603-2

Thermal Properties	dry / cond	Unit	Test Standard
ISO Data			
Melting Temperature (10°C/min)	222 / *	°C	ISO 11357-1/-3
Temp. of deflection under load (1.80 MPa)	55 / *	°C	ISO 75-1/-2
Temp. of deflection under load (0.45 MPa)	145 / *	°C	ISO 75-1/-2
Coeff. of Linear Therm. Expansion, parallel	100 / *	E-6/K	ISO 11359-1/-2
Coeff. of Linear Therm. Expansion, normal	135 / *	E-6/K	ISO 11359-1/-2
Burning Behav. at 1.5 mm Nom. Thickn.	HB / *	class	UL 94
Thickness tested	1.5 / *	mm	-
Oxygen index	22 / *	%	ISO 4589-1/-2

Electrical Properties	dry / cond	Unit	Test Standard
ISO Data			
Relative permittivity, 100Hz	3.7 / 8.5	-	IEC 62631-2-1
Relative permittivity, 1MHz	3.3 / 3.8	-	IEC 62631-2-1
Dissipation Factor, 100Hz	110 / 1650	E-4	IEC 62631-2-1
Dissipation Factor, 1MHz	190 / 660	E-4	IEC 62631-2-1
Volume Resistivity	1E13 / 1E11	Ohm*m	IEC 62631-3-1
Surface Resistivity	* / 1E14	Ohm	IEC 62631-3-2
Electric Strength	35 / 35	kV/mm	IEC 60243-1
Comparative tracking index	600 / -	-	IEC 60112

Other Properties	dry / cond	Unit	Test Standard
ISO Data			
Water Absorption	9 / *	%	Sim. to ISO 62
Humidity absorption	2.7 / *	%	Sim. to ISO 62
Density	1100 / -	kg/m ³	ISO 1183

Test specimen production	Value	Unit	Test Standard
ISO Data			
Injection Molding, melt temperature	270	°C	ISO 294
Injection Molding, mold temperature	80	°C	ISO 294

Durethan® BC30 000000


PA6-I

Envalior


Processing Recommendation Injection Molding	Value	Unit	Test Standard
Pre-drying - Temperature	80	°C	-
Pre-drying - Time	2 - 6	h	-
Processing humidity	≤0.12	%	-
Melt temperature	260 - 280	°C	-
Mold temperature	80 - 90	°C	-

Diagrams


Viscosity-shear rate

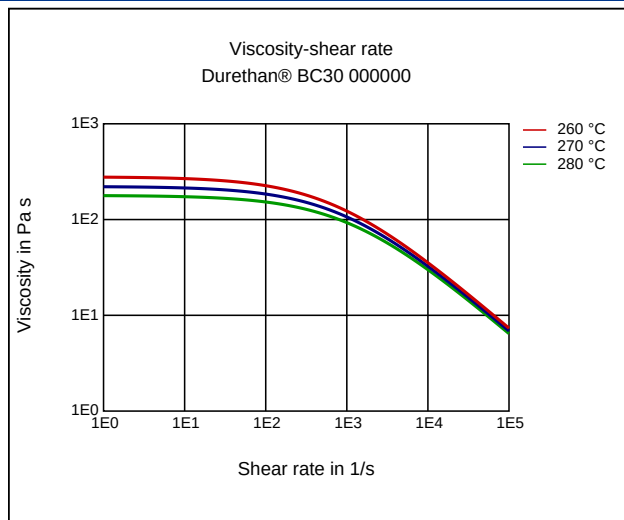


Shearstress-shear rate

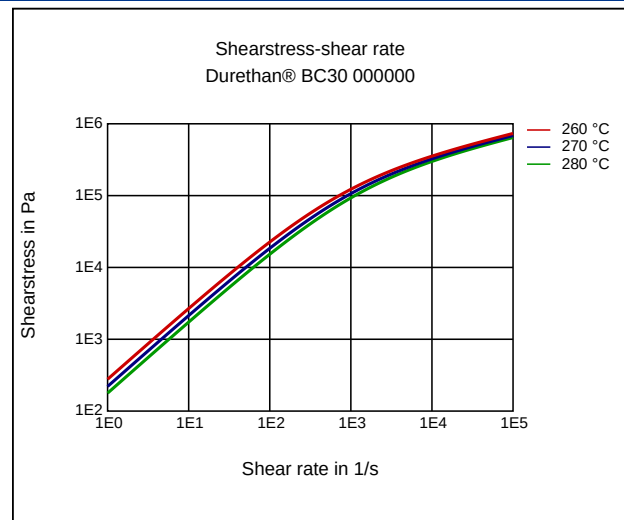

Stress-strain

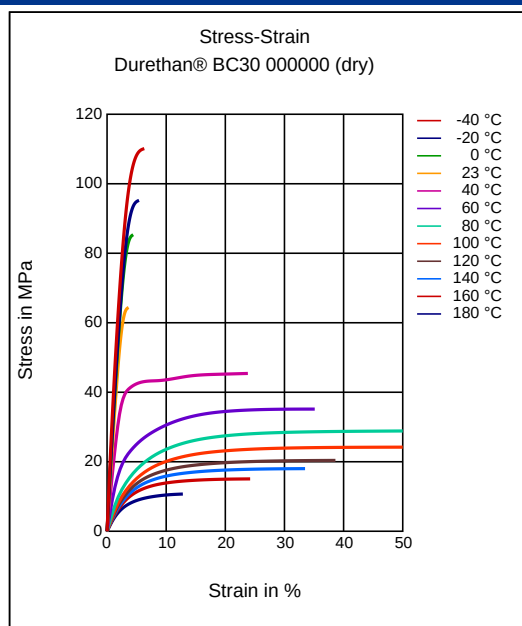

Secant modulus-strain

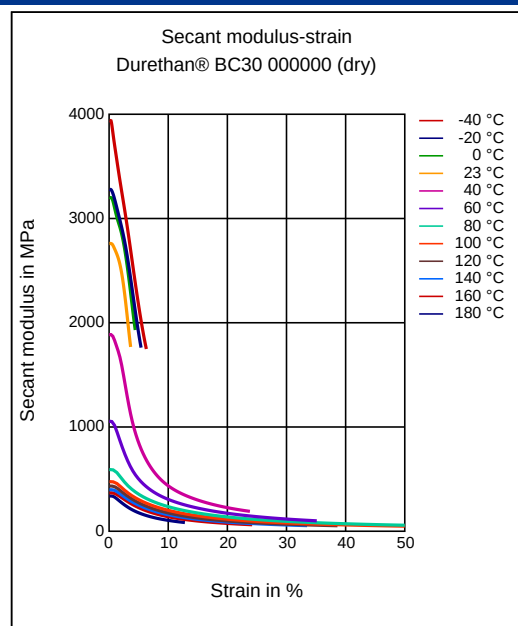

Characteristics

Processing

Injection Molding

Special Characteristics

Impact modified

Durethan® BC30 000000

PA6-I

Envalior

Delivery form

Pellets

Injection Molding

PREPROCESSING

Residual moisture content: 0.03 - 0.12%

Drying temperature dry air dryer: 80 °C

Drying time dry air dryer 2 - 6 h

PROCESSING

Melt temperature (Tmin - Tmax): 260 - 280 °C

Mold temperature: 80 - 90 °C
