

Ultradur® B 4300 K6

PBT-GB30

BASF

Injection molding grade with 30 % glass beads and low warpage tendency. To produce technical parts, e.g. in the automotive or electrical industry. The products with the color designations BK15075 and LS BK15091 are optimized for automotive interior applications

Abbreviated designation according to ISO 1043: PBT-GB30

Rheological properties	Value	Unit	Test Standard
ISO Data			
Melt volume-flow rate, MVR	9	cm ³ /10min	ISO 1133
Temperature	250	°C	-
Load	2.16	kg	-
Molding shrinkage, parallel	1.7	%	ISO 294-4, 2577
Molding shrinkage, normal	1.7	%	ISO 294-4, 2577

Mechanical Properties	Value	Unit	Test Standard
ISO Data			
Tensile Modulus	4000	MPa	ISO 527
Stress at Break	50	MPa	ISO 527
Strain at Break	5	%	ISO 527
Tensile Creep Modulus, 1000h	2200	MPa	ISO 899-1
Impact Strength (Charpy), +23°C	35	kJ/m ²	ISO 179/1eU
Impact Strength (Charpy), -30°C	24	kJ/m ²	ISO 179/1eU
Notched Impact Strength (Charpy), +23°C	3	kJ/m ²	ISO 179/1eA

Thermal Properties	Value	Unit	Test Standard
ISO Data			
Melting Temperature (10°C/min)	223	°C	ISO 11357-1/-3
Temp. of deflection under load (1.80 MPa)	75	°C	ISO 75-1/-2
Temp. of deflection under load (0.45 MPa)	175	°C	ISO 75-1/-2
Burning Behav. at 1.5 mm Nom. Thickn.	HB	class	UL 94
Thickness tested	1.5	mm	-
UL recognition	yes	-	-
Burning Behav. at thickness h	HB	class	UL 94
Thickness tested	0.8	mm	-
UL recognition	yes	-	-
Oxygen index	23	%	ISO 4589-1/-2

Electrical Properties	Value	Unit	Test Standard
ISO Data			
Relative permittivity, 100Hz	3.8	-	IEC 62631-2-1
Relative permittivity, 1MHz	3.8	-	IEC 62631-2-1
Dissipation Factor, 100Hz	12	E-4	IEC 62631-2-1
Dissipation Factor, 1MHz	190	E-4	IEC 62631-2-1
Volume Resistivity	>1E13	Ohm*m	IEC 62631-3-1
Surface Resistivity	1E13	Ohm	IEC 62631-3-2
Electric Strength	37	kV/mm	IEC 60243-1
Comparative tracking index	225	-	IEC 60112

Other Properties	Value	Unit	Test Standard
ISO Data			
Water Absorption	0.4	%	Sim. to ISO 62
Humidity absorption	0.2	%	Sim. to ISO 62
Density	1530	kg/m ³	ISO 1183

Material Specific Properties	Value	Unit	Test Standard
ISO Data			
Viscosity number	113	cm ³ /g	ISO 307, 1157, 1628

Test specimen production	Value	Unit	Test Standard
ISO Data			
Injection Molding, melt temperature	250	°C	ISO 294
Injection Molding, mold temperature	60	°C	ISO 294

Ultradur® B 4300 K6
PBT-GB30


BASF

Injection Molding, injection velocity 200 mm/s ISO 294


Processing Recommendation Injection Molding	Value	Unit	Test Standard
Pre-drying - Temperature	80 - 120	°C	-
Pre-drying - Time	4	h	-
Processing humidity	≤0.04	%	-
Melt temperature	250 - 275	°C	-
Mold temperature	40 - 80	°C	-

Diagrams


Viscosity-shear rate

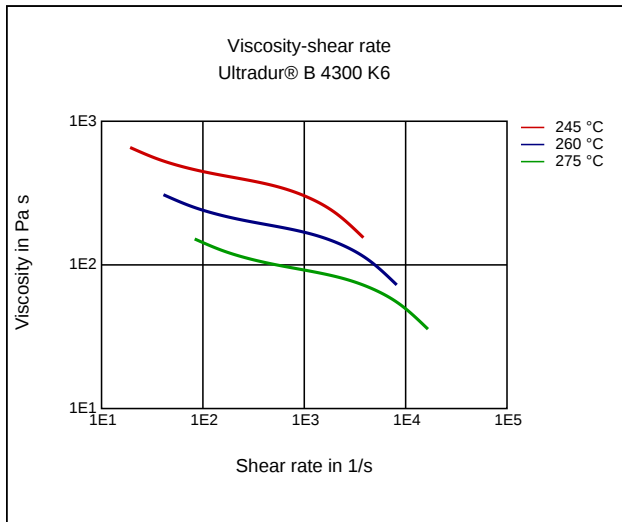


Shearstress-shear rate

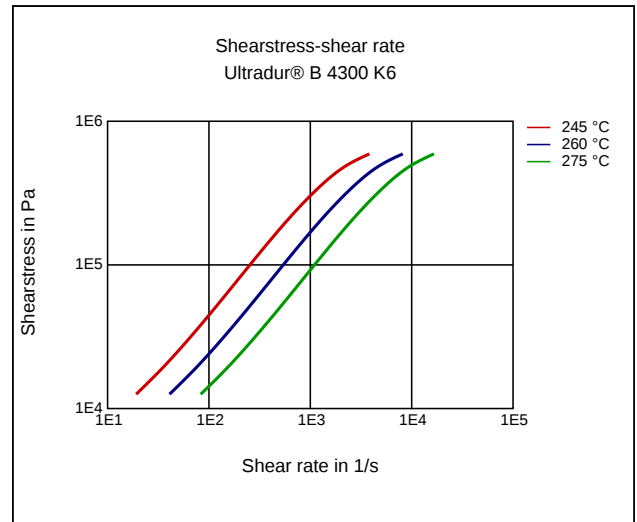

Stress-strain

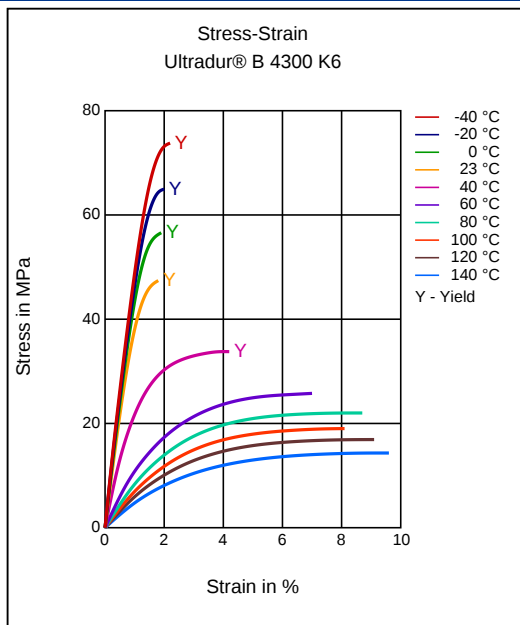


Secant modulus-strain

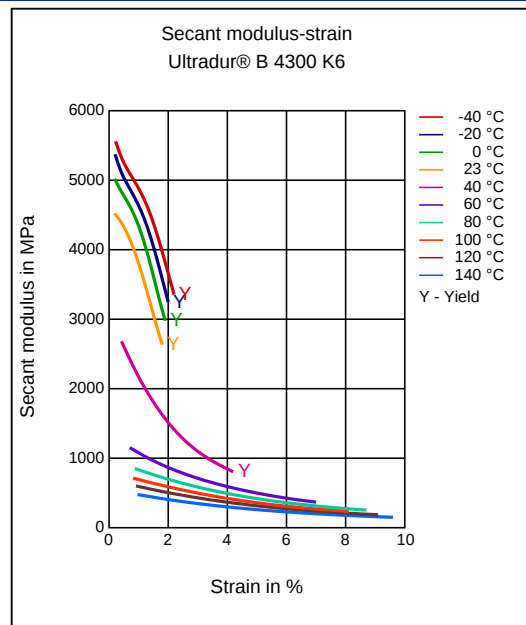


Ultradur® B 4300 K6
PBT-GB30

BASF


Stress-strain (isochronous) 23°C

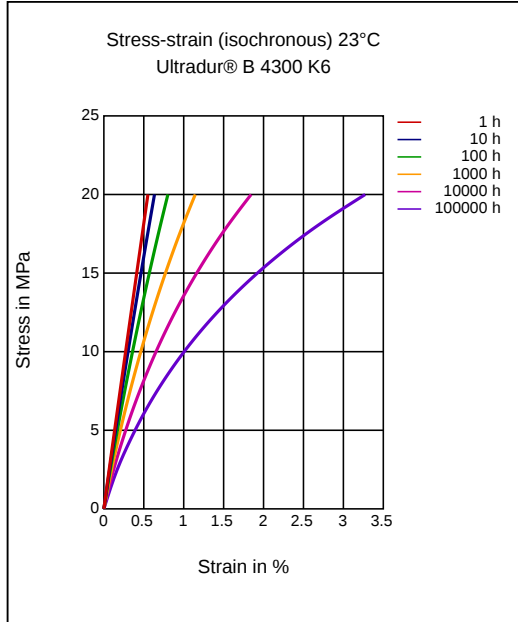


Creep modulus-time 23°C

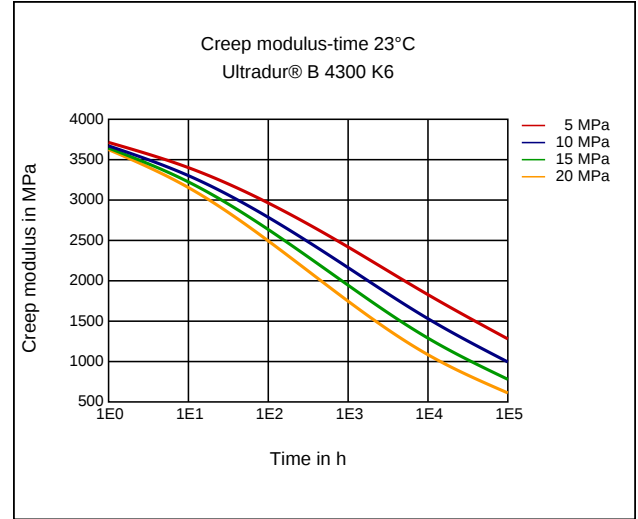

Stress-strain (isochronous) 40°C

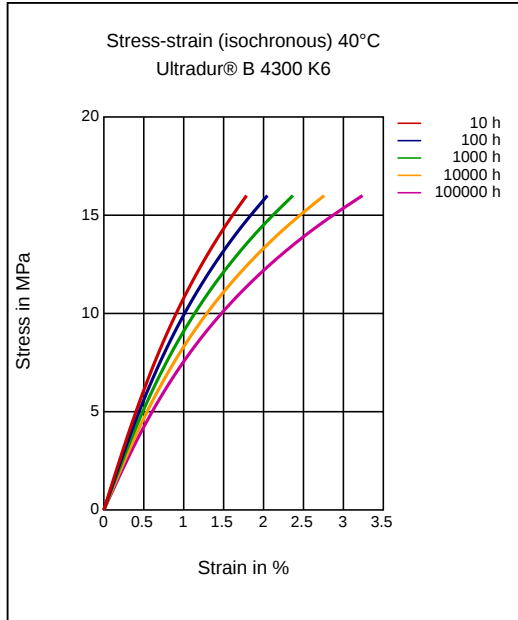


Creep modulus-time 40°C

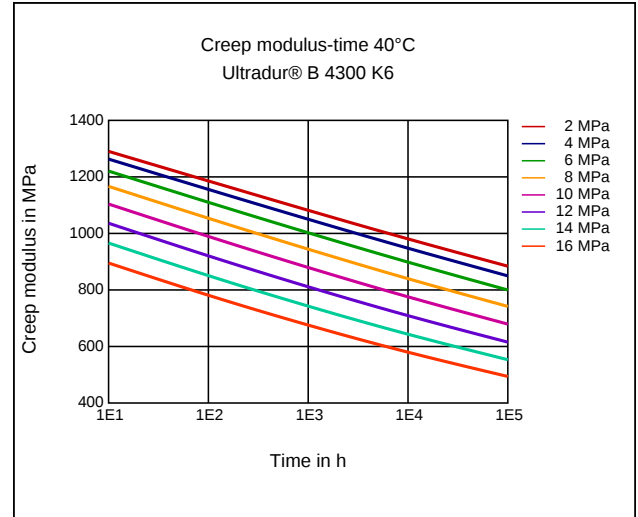


Ultradur® B 4300 K6
PBT-GB30

BASF


Stress-strain (isochronous) 60 °C

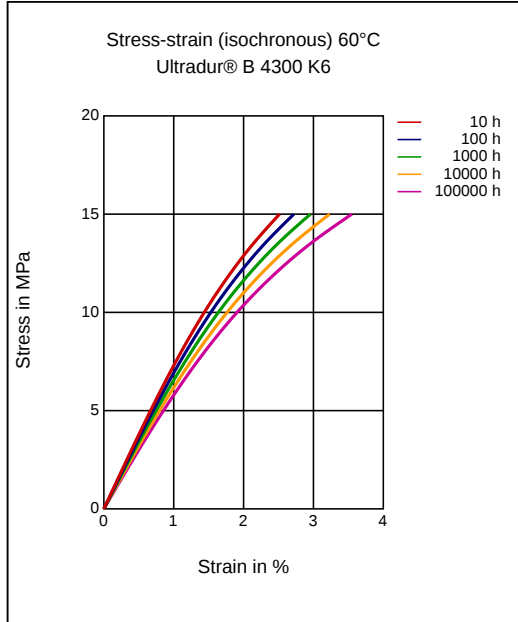


Creep modulus-time 60 °C

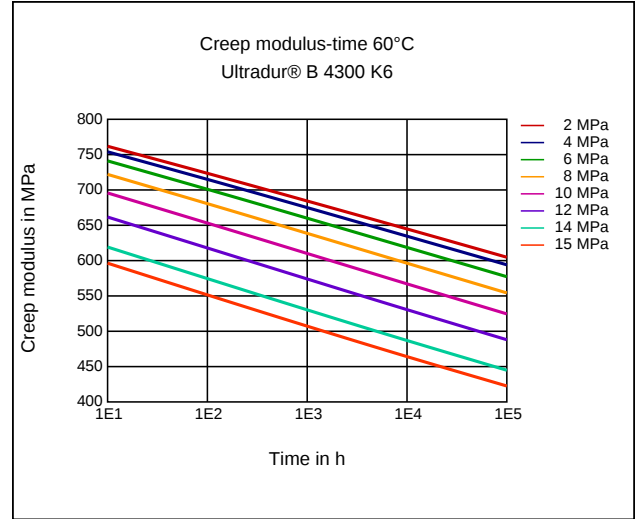

Stress-strain (isochronous) 90 °C

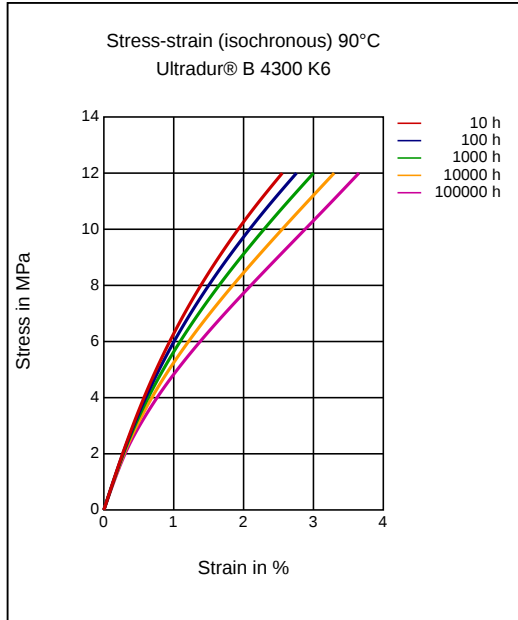


Creep modulus-time 90 °C

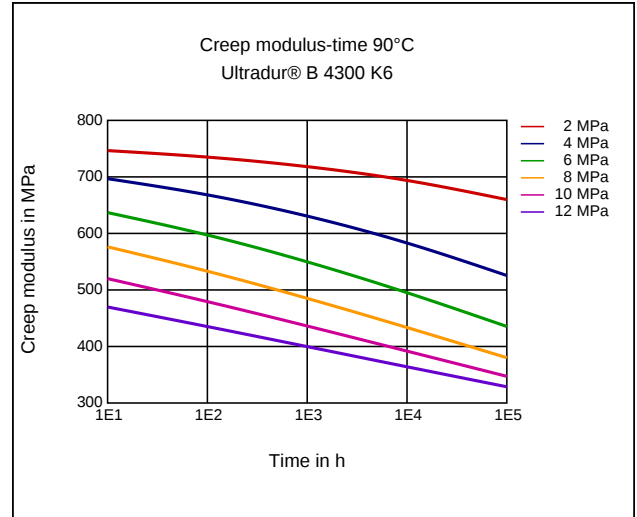


Ultradur® B 4300 K6
PBT-GB30

BASF


Stress-strain (isochronous) 120°C

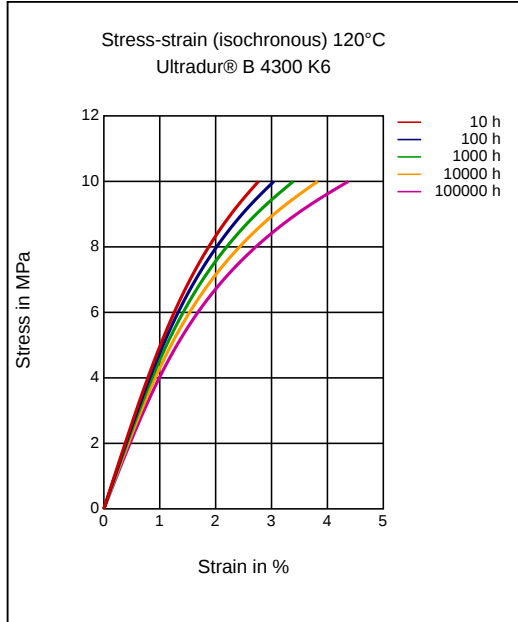


Creep modulus-time 120°C

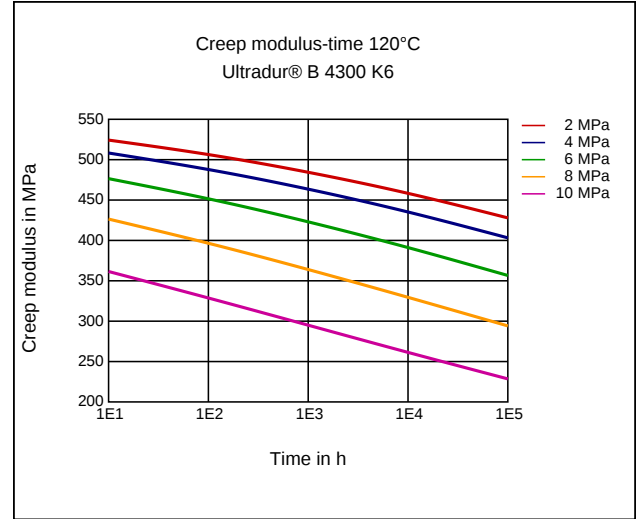

Stress-strain (isochronous) 160°C

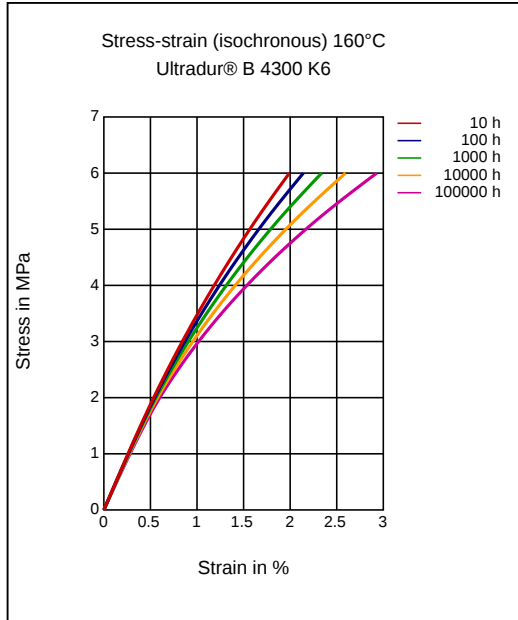

Creep modulus-time 160°C

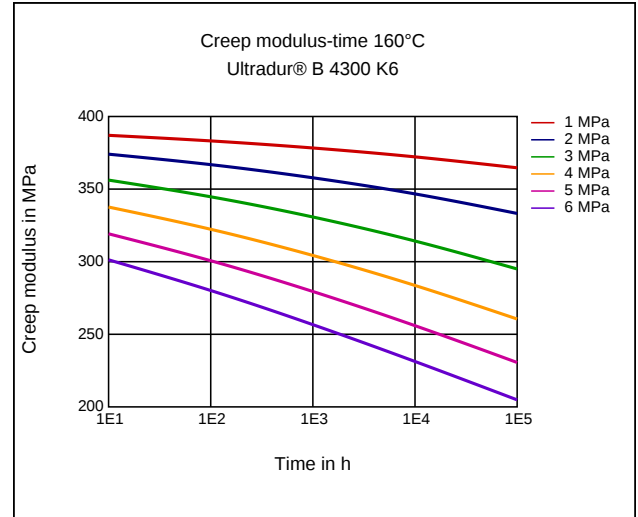


Ultradur® B 4300 K6

PBT-GB30

BASF

Tensile Modulus-Temperature

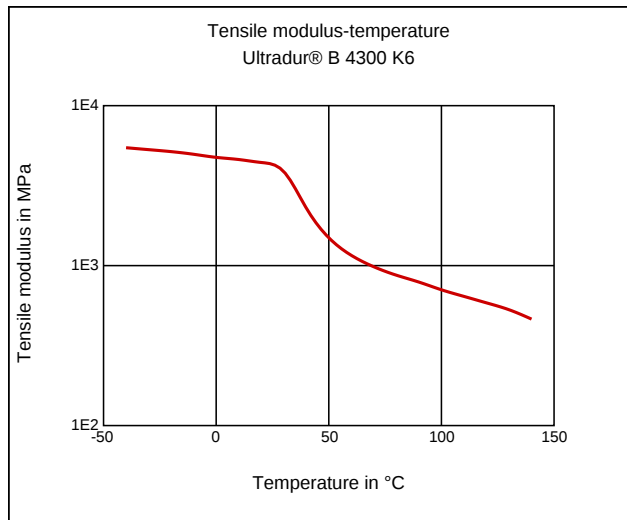

Characteristics

Processing

Injection Molding

Additives

Lubricants

Delivery form

Pellets

Special Characteristics

Light stabilized or stable to light, UV stablized, Heat aging stabilized

Injection Molding

PREPROCESSING

Pre/Post-processing, max. allowed water content: .04 %

Pre/Post-processing, Pre-drying, Temperature: 80 - 120 °C

Pre/Post-processing, Pre-drying, Time: 4 h

PROCESSING

injection molding, Melt temperature, range: 250 - 275 °C

injection molding, Melt temperature, recommended: 250 °C

injection molding, Mold temperature, range: 40 - 80 °C

injection molding, Mold temperature, recommended: 60 °C

Chemical Media Resistance

Acids

- ✓ Acetic Acid (5% by mass) (23°C)