

Ultradur® B 4406 G2

PBT-GF10 FR(17)

BASF

Injection molding grade with 10 % glass fibers for parts requiring enhanced fire resistance (eg relay housings, coil formers, switches, lighting components, plug-and-socket connectors).

Abbreviated designation according to ISO 1043: PBT-GF10 FR(17)

Rheological properties	Value	Unit	Test Standard
ISO Data			
Melt volume-flow rate, MVR	15	cm³/10min	ISO 1133
Temperature	275	°C	-
Load	2.16	kg	-
Molding shrinkage, parallel	1.1	%	ISO 294-4, 2577
Molding shrinkage, normal	1.3	%	ISO 294-4, 2577

Mechanical Properties	Value	Unit	Test Standard
ISO Data			
Tensile Modulus	5500	MPa	ISO 527
Stress at Break	95	MPa	ISO 527
Strain at Break	3.3	%	ISO 527
Impact Strength (Charpy), +23°C	40	kJ/m²	ISO 179/1eU
Impact Strength (Charpy), -30°C	40	kJ/m²	ISO 179/1eU
Notched Impact Strength (Charpy), +23°C	5	kJ/m²	ISO 179/1eA

Thermal Properties	Value	Unit	Test Standard
ISO Data			
Melting Temperature (10°C/min)	223	°C	ISO 11357-1/-3
Temp. of deflection under load (1.80 MPa)	190	°C	ISO 75-1/-2
Temp. of deflection under load (0.45 MPa)	215	°C	ISO 75-1/-2
Coeff. of Linear Therm. Expansion, parallel	51	E-6/K	ISO 11359-1/-2
Coeff. of Linear Therm. Expansion, normal	110	E-6/K	ISO 11359-1/-2
Burning Behav. at 1.5 mm Nom. Thickn.	V-0	class	UL 94
Thickness tested	1.6	mm	-
UL recognition	yes	-	-
Burning Behav. at thickness h	V-0	class	UL 94
Thickness tested	0.4	mm	-
UL recognition	yes	-	-
Burning Behav. 5V at Thickness h	5VA	class	IEC 60695-11-20
Thickness tested	2.0	mm	-
Yellow Card available	yes	-	-
Oxygen index	30	%	ISO 4589-1/-2

Electrical Properties	Value	Unit	Test Standard
ISO Data			
Relative permittivity, 100Hz	3.5	-	IEC 62631-2-1
Relative permittivity, 1MHz	3.5	-	IEC 62631-2-1
Dissipation Factor, 100Hz	80	E-4	IEC 62631-2-1
Dissipation Factor, 1MHz	150	E-4	IEC 62631-2-1
Volume Resistivity	1E13	Ohm*m	IEC 62631-3-1
Surface Resistivity	1E14	Ohm	IEC 62631-3-2
Electric Strength	40	kV/mm	IEC 60243-1
Comparative tracking index	225	-	IEC 60112

Other Properties	Value	Unit	Test Standard
ISO Data			
Water Absorption	0.4	%	Sim. to ISO 62
Humidity absorption	0.2	%	Sim. to ISO 62
Density	1520	kg/m³	ISO 1183

Material Specific Properties	Value	Unit	Test Standard
ISO Data			
Viscosity number	120	cm³/g	ISO 307, 1157, 1628

Ultradur® B 4406 G2

PBT-GF10 FR(17)

BASF


Rheological calculation properties	Value	Unit	Test Standard
ISO Data			
Thermal Conductivity of Melt	1660	W/(m K)	-

Test specimen production	Value	Unit	Test Standard
ISO Data			
Injection Molding, melt temperature	250	°C	ISO 294
Injection Molding, mold temperature	80	°C	ISO 294
Injection Molding, injection velocity	200	mm/s	ISO 294


Processing Recommendation Injection Molding	Value	Unit	Test Standard
Pre-drying - Temperature	80 - 120	°C	-
Pre-drying - Time	4	h	-
Processing humidity	≤0.04	%	-
Melt temperature	250 - 275	°C	-
Mold temperature	60 - 100	°C	-

Diagrams

Viscosity-shear rate

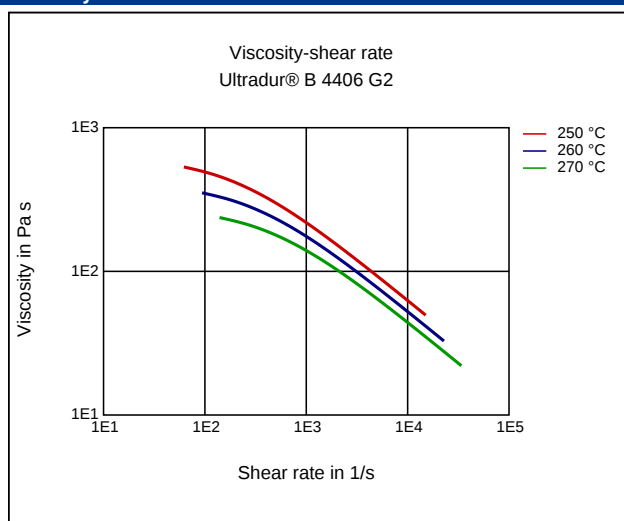

Shearstress-shear rate

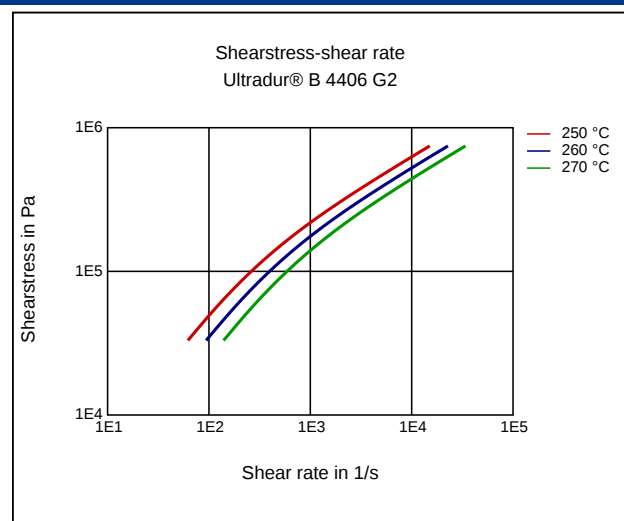


Ultradur® B 4406 G2


PBT-GF10 FR(17)

BASF


Stress-strain

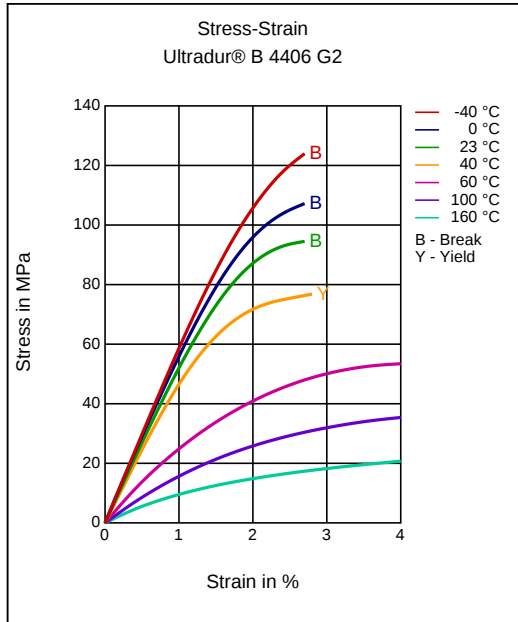


Secant modulus-strain

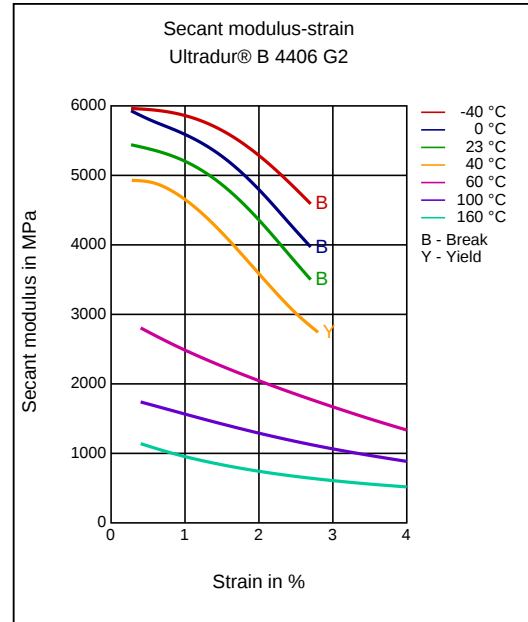

Tensile Modulus-Temperature

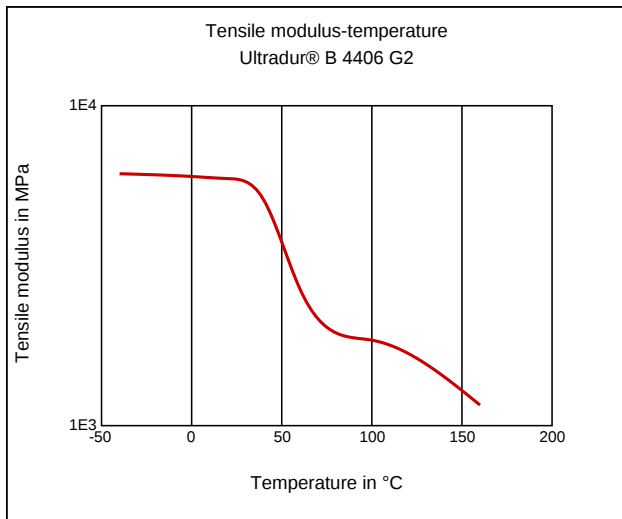

Coeff. of linear thermal expansion, normal

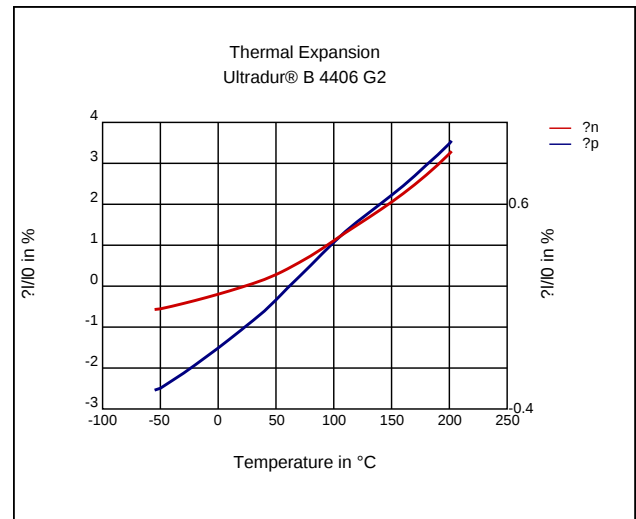

Characteristics

Processing

Injection Molding

Delivery form

Pellets

Additives

Lubricants

Special Characteristics

Flame retardant, Light stabilized or stable to light, UV stabilized, Heat aging stabilized

Injection Molding

PREPROCESSING

Pre/Post-processing, max. allowed water content: .04 %

Pre/Post-processing, Pre-drying, Temperature: 80 - 120 °C

Pre/Post-processing, Pre-drying, Time: 4 h

Ultradur® B 4406 G2

PBT-GF10 FR(17)

BASF

PROCESSING

injection molding, Melt temperature, range: 250 - 275 °C

injection molding, Melt temperature, recommended: 260 °C

injection molding, Mold temperature, range: 60 - 100 °C

injection molding, Mold temperature, recommended: 80 °C

Chemical Media Resistance

Acids

- ✓ Acetic Acid (5% by mass) (23°C)