

# AKROMID®

## B3 GF 50 1 black (2488)

PA6 GF50

AKROMID® B3 GF 50 1 black (2488) is a 50% glass fiber reinforced polyamide 6. It is characterised by a very high stiffness and strength. Furthermore, the material is heat stabilised and therefore perfectly suitable for technical parts in industrial engineering and in the automotive industry.

### Features

heat stabilised 130

### Properties

#### Modulus

17.000 MPa

#### Strength

220 MPa

#### Impact

100 kJ/m<sup>2</sup>

## Mechanical Properties

### Tensile modulus

ISO 527-2

1 mm/min | d.a.m.

17000 MPa

1 mm/min | conditioned

10300 MPa

### Tensile stress at break

ISO 527-2

5 mm/min | d.a.m.

220 MPa

5 mm/min | conditioned

145 MPa

### Tensile strain at break

ISO 527-2

5 mm/min | d.a.m.

2,5 %

5 mm/min | conditioned

4,5 %

### Flexural modulus

ISO 178

2 mm/min | d.a.m.

14900 MPa

### Flexural strength

ISO 178

2 mm/min | d.a.m.

340 MPa

### Charpy impact strength

ISO 179-1/1eU

23°C | d.a.m.

100 kJ/m<sup>2</sup>

23°C | conditioned

110 kJ/m<sup>2</sup>

-30°C | d.a.m.

90 kJ/m<sup>2</sup>

### Charpy notched impact strength

ISO 179-1/1eA

23°C | d.a.m.

20 kJ/m<sup>2</sup>

23°C | conditioned

26 kJ/m<sup>2</sup>

-30°C | d.a.m.

16 kJ/m<sup>2</sup>

---

<b>Ball indentation hardness</b>	961N/30s   d.a.m.	270 MPa
ISO 2039-1		

---

## Thermal Properties

---

<b>Temperature of deflection under load HDT/A</b>	1,8 MPa	220 °C
ISO 75		

---

<b>Temperature of deflection under load HDT/B</b>	0,45 MPa	220 °C
ISO 75		

---

<b>Temperature of deflection under load HDT/C</b>	8 MPa	185 °C
ISO 75		

---

<b>Melting temperature</b>	DSC, 10K/min	220 °C
ISO 11357-3		

---

<b>Coefficient of linear thermal expansion</b>	23°C to 80°C   parallel	0,12 10 <sup>-4</sup> /K
ISO 11359-1/2	23°C to 80°C   transverse	0,98 10 <sup>-4</sup> /K

---

<b>Temperature index for 50% loss of tensile strength</b>	5.000 h	160 - 175 °C
IEC 60216	20.000 h	130 - 150 °C

---

## Flammability

---

<b>Flammability</b>	0,8 mm Wall thickness	HB Class
UL 94		

---

<b>GWFI</b>	1,6 mm Wall thickness	650 °C
IEC 60695-2-12		

---

<b>Burning rate (&lt;100 mm/min)</b>	> 1 mm Thickness	+
FMVSS 302		

---

## General Properties

---

<b>Density</b>	23°C	1,56 g/cm <sup>3</sup>
ISO 1183		

---

<b>Humidity absorption</b>	70°C, 62% r.H.	1,3 - 1,6 %
ISO 1110		

---

<b>Water absorption</b>	23°C, saturated	4,5 - 5,1 %
ISO 62		

---

---

<b>Molding shrinkage</b>	flow	0,1 - 0,3 %
ISO 294-4	transverse	0,4 - 0,6 %

---

## Electrical Properties

---

<b>Volume resistivity</b>	d.a.m.	$10^{13} \Omega \times \text{cm}$
IEC 62631-3-1	conditioned	$10^{10} \Omega \times \text{cm}$

---

<b>Surface resistivity</b>	d.a.m.	$10^{12} \Omega$
IEC 62631-3-2	conditioned	$10^{10} \Omega$


---

<b>Comparative tracking index</b>	Test liquid A	600 V
IEC 60112		

---

## Processing

The values mentioned are recommendations. We only recommend desiccant / dry air dryers or vacuum dryers. Too long a drying time and the resulting residual moisture content below the lower limit can lead to filling problems and surface defects. The specified drying time refers to closed and undamaged bagged material. When processing from previously opened bags or from octabins with polyolefin inliners, a longer drying time may be necessary. It is recommended to check the residual moisture content after the drying process.

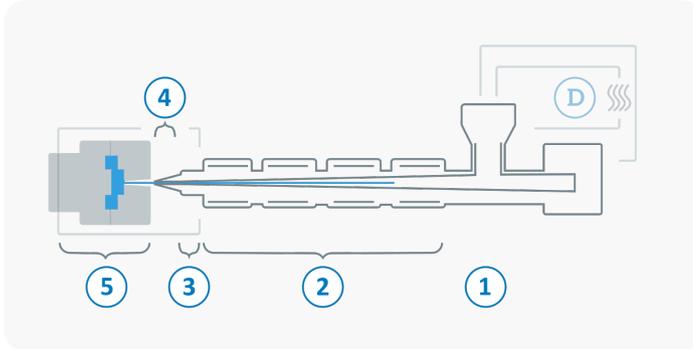

<b>D</b>	Drying time	0 - 4 h
	Drying temperature ( $\tau \leq -30^{\circ}\text{C}$ )	80 °C
	Processing moisture	0,02 - 0,1 %
<b>1</b>	Feed section	60 - 80 °C
<b>2</b>	Temperature Zone 1 - Zone 4	240 - 290 °C
<b>3</b>	Nozzle temperature	260 - 300 °C
<b>4</b>	Melt temperature	270 - 290 °C
<b>5</b>	Mold temperature	80 - 100 °C
<b>→</b>	Holding pressure, spec.	300 - 800 bar
<b>←</b>	Back pressure, spec.	50 - 150 bar
	Injection speed	medium to high
	Screw speed	8 - 15 m/min

## Diagrams

