

## AKROMID®

### B3 GF 50 8 natural (4301)

PA6 GF50

AKROMID® B3 GF 50 8 natural (4301) is a 50% glass fibre reinforced polyamide 6 with very high rigidity and strength. The material corresponds to the European food guideline EU 10/2011 and to the American FDA 21 CFR. This grade is suitable for parts of kitchen and household appliances.

#### Regulatory



#### Properties

Modulus	Strength	Impact
17.000 MPa	240 MPa	100 kJ/m <sup>2</sup>

## Mechanical Properties

<b>Tensile modulus</b> ISO 527-2	1 mm/min   d.a.m.	<b>17000 MPa</b>
	1 mm/min   conditioned	<b>11500 MPa</b>
<b>Tensile stress at break</b> ISO 527-2	5 mm/min   d.a.m.	<b>240 MPa</b>
	5 mm/min   conditioned	<b>160 MPa</b>
<b>Tensile strain at break</b> ISO 527-2	5 mm/min   d.a.m.	<b>3 %</b>
	5 mm/min   conditioned	<b>4,9 %</b>
<b>Flexural modulus</b> ISO 178	2 mm/min   d.a.m.	<b>16000 MPa</b>
	2 mm/min   conditioned	<b>11500 MPa</b>
<b>Flexural strength</b> ISO 178	2 mm/min   d.a.m.	<b>360 MPa</b>
	2 mm/min   conditioned	<b>250 MPa</b>
<b>Charpy impact strength</b> ISO 179-1/1eU	23°C   d.a.m.	<b>100 kJ/m<sup>2</sup></b>
	-30°C   d.a.m.	<b>90 kJ/m<sup>2</sup></b>

## Thermal Properties

<b>Temperature of deflection under load HDT/A</b> ISO 75	1,8 MPa	220 °C
<b>Temperature of deflection under load HDT/B</b> ISO 75	0,45 MPa	220 °C
<b>Temperature of deflection under load HDT/C</b> ISO 75	8 MPa	185 °C
<b>Melting temperature</b> ISO 11357-3	DSC, 10K/min	220 °C
<b>Coefficient of linear thermal expansion</b> ISO 11359-1/2	23°C to 80°C   parallel 23°C to 80°C   transverse	0,11 10 <sup>-4</sup> /K 0,94 10 <sup>-4</sup> /K

## Flammability

<b>Flammability</b> UL 94	1,6 mm Wall thickness	HB Class
<b>GWFI</b> IEC 60695-2-12	1,6 mm Wall thickness	650 °C
<b>Burning rate (&lt;100 mm/min)</b> FMVSS 302	> 1 mm Thickness	+

## General Properties

<b>Density</b> ISO 1183	23°C	1,56 g/cm <sup>3</sup>
<b>Humidity absorption</b> ISO 1110	70°C, 62% r.H.	1,3 - 1,6 %
<b>Water absorption</b> ISO 62	23°C, saturated	4,5 - 5,1 %
<b>Molding shrinkage</b> ISO 294-4	flow transverse	0,1 - 0,3 % 0,4 - 0,6 %

## Electrical Properties


---

<b>Volume resistivity</b> IEC 62631-3-1	d.a.m.	<b>10<sup>13</sup> Ω x cm</b>
<b>Surface resistivity</b> IEC 62631-3-2	d.a.m.	<b>10<sup>12</sup> Ω</b>
<b>Comparative tracking index</b> IEC 60112	Test liquid A	<b>550 V</b>

---

## Processing

The values mentioned are recommendations. We only recommend desiccant / dry air dryers or vacuum dryers. Too long a drying time and the resulting residual moisture content below the lower limit can lead to filling problems and surface defects. The specified drying time refers to closed and undamaged bagged material. When processing from previously opened bags or from octabins with polyolefin liners, a longer drying time may be necessary. It is recommended to check the residual moisture content after the drying process.

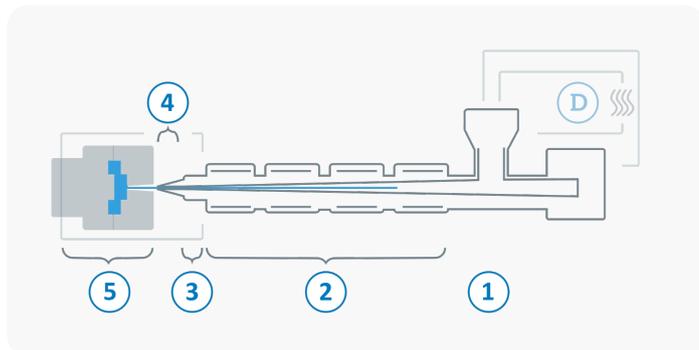

<b>(D)</b> Drying time	0 - 4 h
Drying temperature ( $\tau \leq -30^{\circ}\text{C}$ )	80 °C
Processing moisture	0,02 - 0,1 %
<b>(1)</b> Feed section	60 - 80 °C
<b>(2)</b> Temperature Zone 1 - Zone 4	240 - 290 °C
<b>(3)</b> Nozzle temperature	260 - 300 °C
<b>(4)</b> Melt temperature	270 - 290 °C
<b>(5)</b> Mold temperature	80 - 100 °C
<b>(→)</b> Holding pressure, spec.	300 - 800 bar
<b>(←)</b> Back pressure, spec.	50 - 150 bar
Injection speed	medium to high
Screw speed	8 - 15 m/min

## Diagrams

