

AKROMID® ★

A3 GF 60 1 black (2395)

PA66 GF60

AKROMID® A3 GF 60 1 black (2395) is a 60% glass fibre reinforced and polyamide 6.6 with very high rigidity and strength. Furthermore, the material is heat stabilised and therefore perfectly suitable for technical parts in industrial engineering and in the automotive industry.

Features

heat stabilised 130

Properties



Mechanical Properties

Tensile modulus ISO 527-2	1 mm/min d.a.m.	20500 MPa
	1 mm/min conditioned	15800 MPa
Tensile stress at break ISO 527-2	5 mm/min d.a.m.	260 MPa
	5 mm/min conditioned	190 MPa
Tensile strain at break ISO 527-2	5 mm/min d.a.m.	2 %
	5 mm/min conditioned	2,5 %
Flexural modulus ISO 178	2 mm/min d.a.m.	19800 MPa
Flexural strength ISO 178	2 mm/min d.a.m.	400 MPa
Charpy impact strength ISO 179-1/1eU	23°C d.a.m.	85 kJ/m ²
	23°C conditioned	95 kJ/m ²
	-30°C d.a.m.	95 kJ/m ²
Charpy notched impact strength ISO 179-1/1eA	23°C d.a.m.	19 kJ/m ²
	23°C conditioned	22 kJ/m ²
	-30°C d.a.m.	19 kJ/m ²

Ball indentation hardness	961N/30s d.a.m.	330 MPa
ISO 2039-1		

Thermal Properties

Temperature of deflection under load HDT/A	1,8 MPa	260 °C
ISO 75		

Temperature of deflection under load HDT/B	0,45 MPa	260 °C
ISO 75		

Temperature of deflection under load HDT/C	8 MPa	235 °C
ISO 75		

Melting temperature	DSC, 10K/min	262 °C
ISO 11357-3		

Coefficient of linear thermal expansion	23°C to 80°C parallel	0,12 10 ⁻⁴ /K
ISO 11359-1/2	23°C to 80°C transverse	0,82 10 ⁻⁴ /K

Temperature index for 50% loss of tensile strength	5.000 h	150 °C
IEC 60216		

Flammability

Flammability	1,6 mm Wall thickness	HB Class
UL 94		

GWFI	1,6 mm Wall thickness	650 °C
IEC 60695-2-12		

GWIT	1,6 mm Wall thickness	675 °C
IEC 60695-2-13		

Burning rate (<100 mm/min)	> 1 mm Thickness	+
FMVSS 302		

General Properties

Density	23°C	1,71 g/cm ³
ISO 1183		

Humidity absorption	70°C, 62% r.H.	1,0 - 1,2 %
ISO 1110		

Water absorption ISO 62	23°C, saturated	3,2 - 3,7 %
Molding shrinkage ISO 294-4	flow transverse	0,1 - 0,3 % 0,4 - 0,6 %

Electrical Properties


Volume resistivity IEC 62631-3-1	d.a.m. conditioned	10¹³ Ω x cm 10¹⁰ Ω x cm
Surface resistivity IEC 62631-3-2	d.a.m. conditioned	10¹² Ω 10¹⁰ Ω
Comparative tracking index IEC 60112	Test liquid A	600 V

Rheological Properties

Flowability AKRO	2 mm Thickness	300 mm
----------------------------	----------------	---------------

Processing

The values mentioned are recommendations. We only recommend desiccant / dry air dryers or vacuum dryers. Too long a drying time and the resulting residual moisture content below the lower limit can lead to filling problems and surface defects. The specified drying time refers to closed and undamaged bagged material. When processing from previously opened bags or from octabins with polyolefin inliners, a longer drying time may be necessary. It is recommended to check the residual moisture content after the drying process.

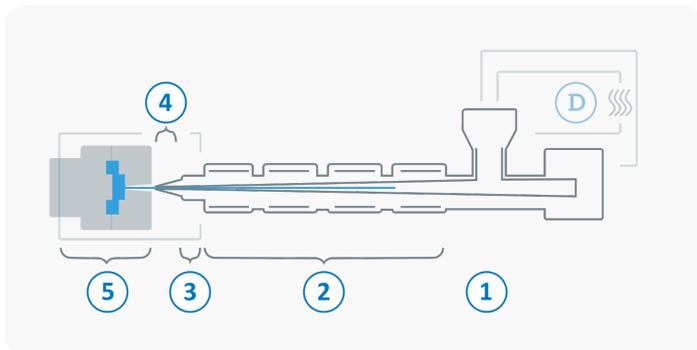

D	Drying time	0 - 4 h
	Drying temperature ($\tau \leq -30^\circ\text{C}$)	80 °C
	Processing moisture	0,02 - 0,1 %
1	Feed section	60 - 80 °C
2	Temperature Zone 1 - Zone 4	260 - 300 °C
3	Nozzle temperature	270 - 310 °C
4	Melt temperature	280 - 300 °C
5	Mold temperature	80 - 100 °C
→	Holding pressure, spec.	300 - 800 bar
←	Back pressure, spec.	50 - 150 bar
	Injection speed	medium to high
	Screw speed	8 - 15 m/min

Diagrams

