

CELANEX® 3300-2

CELANEX® PBT

Celanex 3300-2 is a general purpose, 30% glass reinforced, polybutylene terephthalate that offers a superior combination of mechanical, electrical, and thermal properties. This grade provides outstanding processability and good chemical resistance. Celanex 3300-2 is a high flow material that contains an internal lubricant.

Product information

Resin Identification	PBT-GF30	ISO 1043
Part Marking Code	>PBT-GF30<	ISO 11469

Rheological properties

Melt volume-flow rate	16 cm ³ /10min	ISO 1133
Temperature	250 °C	
Load	2.16 kg	
Melt mass-flow rate, Temperature	250 °C	
Melt mass-flow rate, Load	2.16 kg	
Viscosity number	100 cm ³ /g	ISO 307, 1628
Intrinsic viscosity	0.75	ISO 307, 1628
Moulding shrinkage range, parallel	0.3 - 0.7 %	ISO 294-4, 2577
Moulding shrinkage range, normal	0.7 - 1.1 %	ISO 294-4, 2577

Typical mechanical properties

Tensile modulus	9900 MPa	ISO 527-1/-2
Tensile stress at break, 5mm/min	140 MPa	ISO 527-1/-2
Tensile strain at break, 5mm/min	2.5 %	ISO 527-1/-2
Flexural modulus	9700 MPa	ISO 178
Flexural strength	210 MPa	ISO 178
Charpy impact strength, 23°C	46 kJ/m ²	ISO 179/1eU
Charpy impact strength, -30°C	40 kJ/m ²	ISO 179/1eU
Charpy notched impact strength, 23°C	9.2 kJ/m ²	ISO 179/1eA
Charpy notched impact strength, -30°C	8.5 kJ/m ²	ISO 179/1eA
Izod notched impact strength, 23°C	7.5 kJ/m ²	ISO 180/1A
Izod impact strength, 23°C	24 kJ/m ²	ISO 180/1U
Hardness, Rockwell, M-scale	90	ISO 2039-2
Poisson's ratio	0.4	

Thermal properties

Melting temperature, 10°C/min	225 °C	ISO 11357-1/-3
Glass transition temperature, 10°C/min	60 °C	ISO 11357-1/-3
Temperature of deflection under load, 1.8 MPa	205 °C	ISO 75-1/-2
Temperature of deflection under load, 0.45 MPa	225 °C	ISO 75-1/-2
Temperature of deflection under load, 8 MPa	150 °C	ISO 75-1/-2
Vicat softening temperature, 50°C/h 50N	220 °C	ISO 306
Coefficient of linear thermal expansion (CLTE), parallel	25 E-6/K	ISO 11359-1/-2
Coefficient of linear thermal expansion (CLTE), normal	100 E-6/K	ISO 11359-1/-2

CELANEX® 3300-2

CELANEX® PBT

Flammability

Burning Behav. at thickness h	HB class	IEC 60695-11-10
Thickness tested	0.71 mm	IEC 60695-11-10
Oxygen index	20 %	ISO 4589-1/-2
FMVSS Class	B	ISO 3795 (FMVSS 302)
Burning rate, Thickness 1 mm	55 mm/min	ISO 3795 (FMVSS 302)

Electrical properties

Relative permittivity, 100Hz	4.5	IEC 62631-2-1
Relative permittivity, 1MHz	4.1	IEC 62631-2-1
Dissipation factor, 100Hz	22 E-4	IEC 62631-2-1
Dissipation factor, 1MHz	160 E-4	IEC 62631-2-1
Volume resistivity	>1E13 Ohm.m	IEC 62631-3-1
Surface resistivity	>1E15 Ohm	IEC 62631-3-2
Electric strength	31 kV/mm	IEC 60243-1

Physical/Other properties

Humidity absorption, 2mm	0.2 %	Sim. to ISO 62
Water absorption, 2mm	0.4 %	Sim. to ISO 62
Water absorption, Immersion 24h	0.07 %	Sim. to ISO 62
Density	1530 kg/m ³	ISO 1183

Injection

Drying Recommended	yes
Drying Temperature	120 °C
Drying Time, Dehumidified Dryer	4 h
Processing Moisture Content	≤0.02 %
Melt Temperature Optimum	250 °C
Min. melt temperature	240 °C
Max. melt temperature	260 °C
Screw tangential speed	0.1 - 0.3 m/s
Mold Temperature Optimum	80 °C
Min. mould temperature	60 °C
Max. mould temperature	130 °C
Ejection temperature	185 °C

Characteristics

Processing	Injection Moulding
Delivery form	Pellets
Additives	Release agent

Additional information

Injection molding

Preprocessing

To avoid hydrolytic degradation during processing, CELANEX resins have to be dried to a moisture level equal to or less than 0.02%. Drying should be done in a

CELANEX® 3300-2

CELANEX® PBT

dehumidifying hopper dryer capable of dewpoints <-30°F (-34°C) at 250°F (121°C) for 4 hours.

Processing

Rear Temperature 450-470(230-240) deg F (deg C)
Center Temperature 460-480(235-250) deg F (deg C)
Front Temperature 470-500(240-260) deg F (deg C)
Nozzle Temperature 480-500(250-260) deg F (deg C)
Melt Temperature 460-500(235-260) deg F (deg C)
Mold Temperature 150-200(65-93) deg F (deg C)
Back Pressure 0-50 psi
Screw Speed Medium
Injection Speed Fast

Injection speed, injection pressure and holding pressure have to be optimized to the individual article geometry. To avoid material degradation during processing low back pressure and minimum screw speed have to be used. Overheating of the material has to be avoided, in particular for flame retardant grades. Up to 25% clean and dry regrind may be used.

Processing Notes

Pre-Drying

To avoid hydrolytic degradation during processing, CELANEX resins have to be dried to a moisture level equal to or less than 0.02%. Drying should be done in a dehumidifying hopper dryer capable of dewpoints <-40°F (-40°C) at 250°F (121°C) for 4 hours.

Storage

For subsequent storage of the material in the dryer until processed (<= 60 h) it is necessary to lower the temperature to 100° C.

Automotive

OEM	STANDARD	ADDITIONAL INFORMATION
Continental	TST N 055 47.12	(TST N 055 47.12-000)
Ford	WSS-M4D725-B1	
Ford	WSS-M4D929-A3	Natural
Ford	WSS-M4D929-A3	Black
General Motors	GMW16733P-PBT-GF30	N/A
Hyundai	MS941-03 Type F-5	
Li Auto	Q/LiA5310038	2021 (V2)
Nissan	PBTP(G)-1NX-30	

CELANEX® 3300-2

CELANEX® PBT

Nissan

Renault

SAIC Motor

Stellantis

Stellantis - Chrysler

PBTP(G30)-1NX-1

No Spec, Special Part Approval, See Your CE
Account Manager.

SMTC 5 310 038

MS.90181 / PBT.GF30.8000T.7C.HS


MS.50103 / CPN-2252

ED3002 Black

CPN 2252 NATURAL or CPN2512 Black ???

Natural


Stress-strain

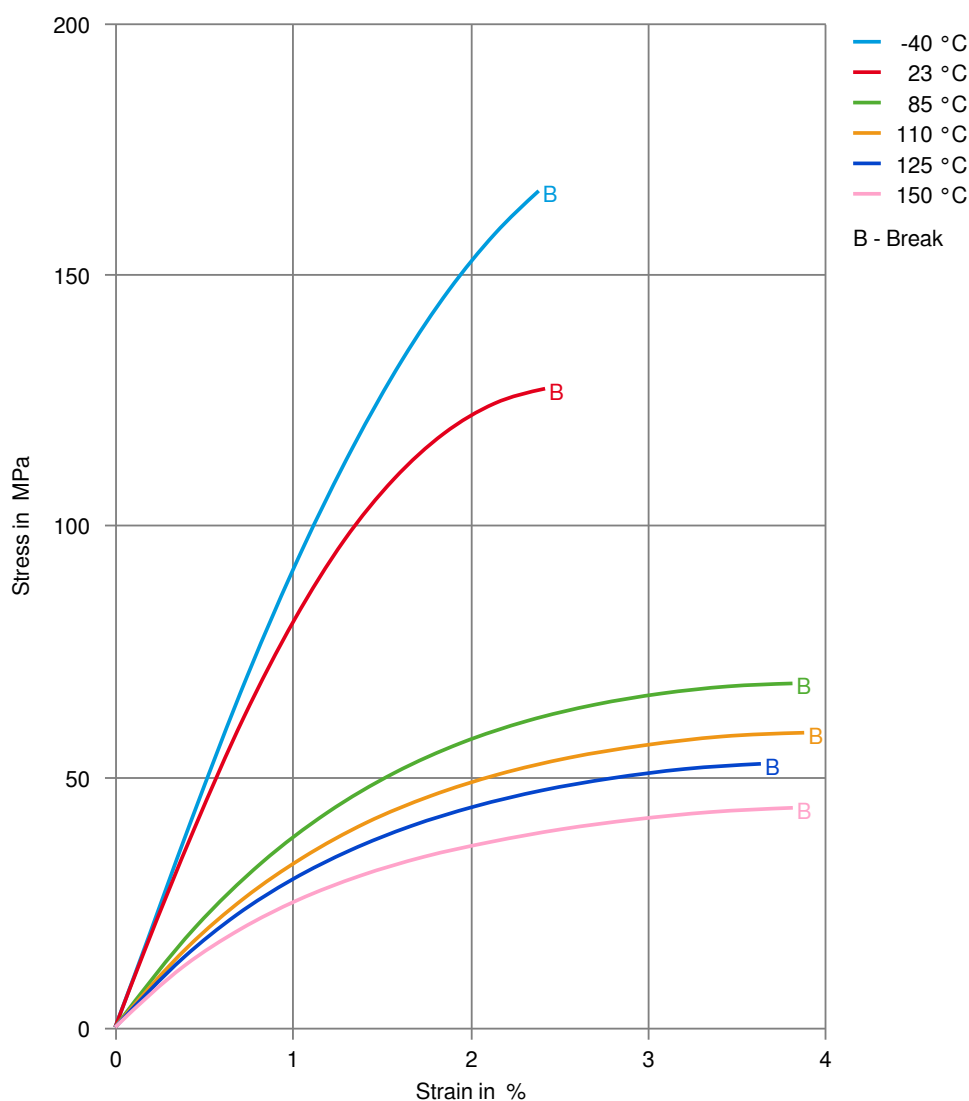

CELANEX® 3300-2

CELANEX® PBT

Secant modulus-strain

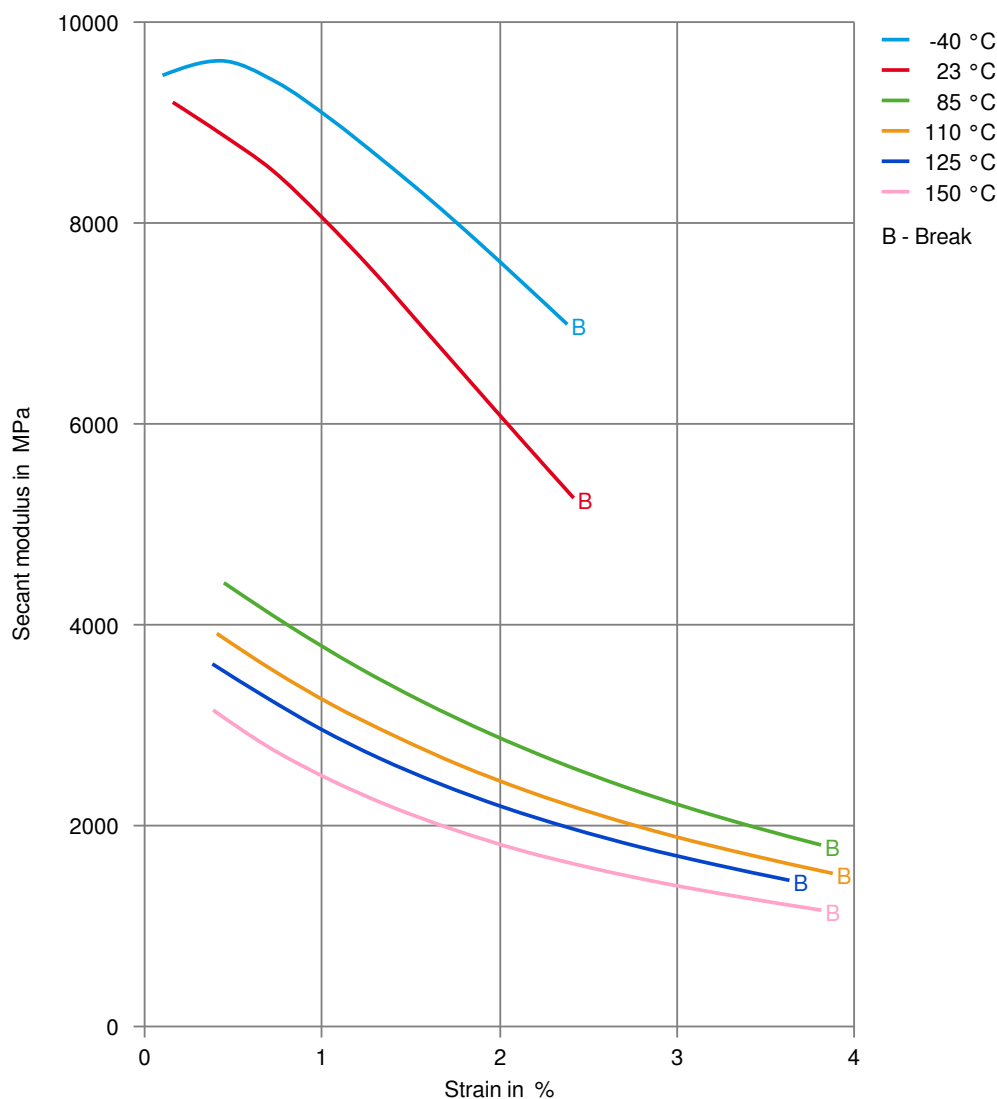

Printed: 2025-05-30

Page: 5 of 5

Revised: 2025-05-16 Source: Celanese Materials Database

NOTICE TO USERS: Values shown are based on testing of laboratory test specimens and represent data that fall within the standard range of properties for natural material. These values alone do not represent a sufficient basis for any part design and are not intended for use in establishing maximum, minimum, or ranges of values for specification purposes. Colourants or other additives may cause significant variations in data values. Properties of moulded parts can be influenced by a wide variety of factors including, but not limited to, material selection, additives, part design, processing conditions and environmental exposure. Other than those products expressly identified as medical grade (including by MT® product designation or otherwise), Celanese's products are not intended for use in medical or dental implants. Regardless of any such product designation, any determination of the suitability of a particular material and part design for any use contemplated by the users and the manner of such use is the sole responsibility of the users, who must assure themselves that the material as subsequently processed meets the needs of their particular product or use. To the best of our knowledge, the information contained in this publication is accurate; however, we do not assume any liability whatsoever for the accuracy and completeness of such information. The information contained in this publication should not be construed as a promise or guarantee of specific properties of our products. It is the sole responsibility of the users to investigate whether any existing patents are infringed by the use of the materials mentioned in this publication. Moreover, there is a need to reduce human exposure to many materials to the lowest practical limits in view of possible adverse effects. To the extent that any hazards may have been mentioned in this publication, we neither suggest nor guarantee that such hazards are the only ones that exist. We recommend that persons intending to rely on any recommendation or to use any equipment, processing technique or material mentioned in this publication should satisfy themselves that they can meet all applicable safety and health standards. We strongly recommend that users seek and adhere to the manufacturer's current instructions for handling each material they use, and entrust the handling of such material to adequately trained personnel only. Please call the telephone numbers listed for additional technical information. Call Customer Services for the appropriate Materials Safety Data Sheets (MSDS) before attempting to process our products.

© 2025 Celanese or its affiliates. All rights reserved. Celanese®, registered C-ball design and all other trademarks identified herein with ®, TM, SM, unless otherwise noted, are trademarks of Celanese or its affiliates. Fortron is a registered trademark of Fortron Industries LLC.